

ARMY RESEARCH LABORATORY



Dynamic Deformation of a Ceramic/ GRP Composite From KE Impact

E. Straßburger
H. Senf

ARL-CR-282

January 1996

prepared by

**Fraunhofer-Institut Für Kurzzeitdynamik
Ernst Mach Institut
Hauptstrasse 18
D 79 576 Weil am Rhein
Germany**

under contract

DAJA45-93-C-0045

REFERENCE COPY
DOES NOT CIRCULATE

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED.

OCT 1996

NOTICES

Destroy this report when it is no longer needed. DO NOT return it to the originator.

Additional copies of this report may be obtained from the National Technical Information Service, U.S. Department of Commerce, 5285 Port Royal Road, Springfield, VA 22161.

The findings of this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

The use of trade names or manufacturers' names in this report does not constitute indorsement of any commercial product.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project(0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE January 1996		3. REPORT TYPE AND DATES COVERED Final, September 1993 - May 1995
4. TITLE AND SUBTITLE Dynamic Deformation of a Ceramic/GRP Composite From KE Impact			5. FUNDING NUMBERS C: DAJA45-93-C-0045	
6. AUTHOR(S) E. StraBburger and H. Senf				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Fraunhofer-Institut Fuer Kurzzeitdynamik Ernst-Mach-Institut Weil am Rhein, Germany			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-CR-282	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WT-TA Aberdeen Proving Ground, MD 21005-5066			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Point of contact for this report is William A. Gooch, Jr., U.S. Army Research Laboratory, ATTN: AMSRL-WT-TA, Aberdeen Proving Ground, MD 21005-5066.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Ceramic/GRP (Glass Reinforced Plastic) composite targets were impacted by hemispherically nosed tungsten alloy projectiles (L = 55 mm, D = 17 mm, m = 214 g) at velocities of about 1000 m/s. The impact velocities were chosen close to the ballistic limit of this projectile-target combination, which was determined from parametric tests conducted by the U.S. Army Research Laboratory, Aberdeen Proving Ground, Maryland, USA. The GRP laminates were S-2 Glass/Polyester fabricated by Simula, Inc. of Phoenix, Arizona, USA. Simula also glued the ceramic tiles to the S-2 glass using standard assembly techniques to maintain a consistent bond-interface thickness. The ceramic used in these tests was sintered AD995 alumina produced by Coors Ceramic of Golden, Colorado, USA. The 152-mm x 152-mm- and 40-mm-thick ceramic tiles were confined in a steel frame and glued to the 40-mm-thick GRP panels. The GRP panels were in two sizes: 300 mm x 300 mm or 600 mm x 600 mm square. The dynamic bulging of the GRP panels during penetration was observed by means of two Cranz-Schardin high-speed cameras in side view and top view simultaneously. Distance-time curves of the bulging of the GRP panels are derived from the camera recordings for both panel sizes, and the damage of the targets is described.				
14. SUBJECT TERMS ceramic/GRP composites, ballistic limit, high-speed photography, dynamic bulging, laminate targets, delamination, alumina			15. NUMBER OF PAGES 47	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK.

PREFACE

The U.S. Army Research Laboratory (ARL) has an ongoing effort to analyze the kinetics of a ceramic/glass-reinforced plastic (GRP) composite when impacted by a kinetic energy penetrator. This work documents the time-derived dynamic deformation of the rear composite when impacted by nonperforating L/D 3.2 tungsten penetrators (17 mm ϕ x 55 mm, 214 g) at impact velocities of about 1,000 m/s. This research was conducted for ARL by the Fraunhofer-Institut für Kurzzeitdynamik Ernst-Mach-Institut, Weil am Rhein, Germany, between September 1993 and May 1995. The images were obtained with the state-of-the-art, high-speed photographic capability available at the Ernst-Mach-Institut, specifically two 24-spark Craz-Schardin cameras. This equipment allows observation of up to 24 time-derived images at predetermined time intervals of less than 1 μ s, if desired. In this analysis, the time intervals were increased to allow observation of the dynamic bulging of the rear GRP/composite in both the horizontal and vertical planes over long time intervals of up to 1,800 μ s. The composite panels were of two sizes—300 mm x 300 mm and 600 mm x 600 mm—and were attached to the steel test frame by different techniques. One goal of this work was to examine the effect of panel size and attachment techniques on the dynamic bulge. From these data, the time delay of the initial bulging of the rear face of the composite, the bulge velocity, and maximum bulge height could be determined. Since the majority of these tests were nonperforating impacts and the penetration velocity of this projectile into the ceramic is known, further insight into the kinetic transfer to the composite is possible.

This ARL report provides a greater dissemination of the final report of Contract DAJA 45-93-C-0045, prepared for the European Research Office (ERO) of the U.S. Army, which oversaw the contract for the Armor Mechanics Branch, Terminal Effects Division, Weapons Technology Directorate of ARL. The Armor Mechanics Branch would like to specifically thank Dr. Roy Reichenbach of ERO for his assistance in this matter.

The Armor Mechanics Branch would also like to acknowledge the long-term professional interaction with Mr. Senf and Mr. Straßburger, which has led to many fruitful technical exchanges during the course of this work.

Any questions or request for clarifications can be directed to Mr. William Gooch, Armor Mechanics Branch, (410) 278-6080.

INTENTIONALLY LEFT BLANK.

TABLE OF CONTENTS

	<u>Page</u>
PREFACE	iii
LIST OF FIGURES	vii
LIST OF TABLES	viii
1. INTRODUCTION	1
2. EXPERIMENTAL PROGRAM AND RESULTS	1
3. SUMMARY	33
ACKNOWLEDGEMENT	33
DISTRIBUTION LIST	35

INTENTIONALLY LEFT BLANK.

LIST OF FIGURES

<u>Figure</u>	<u>Page</u>
2.1 Schematic of the experimental configuration	2
2.2 Shadowgraphs of shot no. 10968	
Side view	4
Top view	5
2.3 Distance-time curves of shot 10968	6
2.4 Photographs of the impacted target, shot no. 10968	
a) Impacted side	7
b) Side view, showing the delamination	7
2.5 Shadowgraphs of shot No. 10997	
a) Side view	9
b) Top view	10
2.6 Distance-time curves of shot no. 10997	11
2.7 Photographs of the impacted target, shot no. 10997	
a) Impacted view	12
b) Side view, no delamination	12
2.8 Shadowgraphs of shot no. 11000	13
2.9 Distance-time curve of shot no. 11000	14
2.10 Photographs of the impacted target, shot no. 11000	
a) Impacted side	15
b) Side view	15
2.11 Shadowgraphs of shot no. 10973	
a) Side view	17
b) Top view	18
2.12 Distance-time curves of shot no. 10973	19
2.13 Photographs of the impacted target, shot no. 10973	20
2.14 Shadowgraphs of shot no. 10994	
a) Side view	21
b) Top view	22
2.15 Distance-time curves of shot no. 10994	23

<u>Figure</u>	<u>Page</u>
2.16 Photographs of the impacted target, shot no. 10994	
a) Impacted side	24
b) Side view, showing the delamination	24
2.17 Shadowgraphs of shot no. 10998	26
2.18 Distance-time curves of shot no. 10998	27
2.19 Photographs of the impacted target, shot no. 10998	28
2.20 Shadowgraphs of shot no. 10999	
a) Side view	29
b) Top view	30
2.21 Distance-time curves of shot no. 10999	31
2.22 Photographs of the impacted target, shot no. 10999	
a) Back side	32
b) Side view	32

LIST OF TABLES

<u>Table</u>	<u>Page</u>
2.1 Experimental data	3

1 Introduction

Modern armour components usually consist of several layers of various materials with different functions. The backing layer at the rear has to support the front layers and to defeat the residual projectile and fragments generated during penetration. In order to fulfill these requirements the backing material must exhibit not only a high strength but also a sufficient stiffness. Appropriate non-metallic materials for this purpose are for example fiberglass reinforced plastics (GRP). It is not only necessary to know if the projectile is stopped but also how much the armor is bulged during impact in order to guarantee the protection of the crew of an armored vehicle or the electronic equipment behind the armor. Since there is only very little data available on the ballistic performance GRP and composites with a GRP layer it was of great interest to generate a set of data on the kinetics of ceramic/GRP targets under impact. Particularly the influence of the size of the backing GRP panels on the performance of the targets was investigated in this study.

2 Experimental Program and Results

Four 12" x 12" x 1.5" GRP (Glass Reinforced Plastics) panels with a 152 mm x 152 mm x 40 mm aluminumoxide tile attached and three 24" x 24" x 1.5" GRP panels with 152 mm x 152 mm x 40 mm alumina tiles attached to each were delivered to EMI for ballistic testing. The GRP laminates were S-2 Glass/Polyester fabricated by Simula Incorporated of Phoenix, Arizona, USA. Simula also glued the ceramic tiles to the S-2 glass using standard assembly techniques to maintain a consistent bond-interface thickness. The ceramic tiles were confined by a steel frame of 23 mm thickness. The thickness of the epoxy joint between the tiles and the confinement was approximately 2 to 3 mm. During the tests the Ceramic/GRP panels were fixed to a steel frame by screws.

In all experiments the 55 W hemispherically nosed tungsten alloy penetrator was used. The length of the projectile is 55 mm, the diameter 17 mm and the mass is 214 g. The impact velocities were chosen close to the ballistic limit, which was expected to be 1076 m/s. The ballistic limit velocity was determined from parametric tests conducted by the U.S. Army Research Laboratory, Aberdeen Proving Ground, Maryland, USA.

A schematic of the experimental configuration is shown in Figure 2.1. The bulging of the GRP panels was observed by means of two Craz-Schardin cameras in side view and top view simultaneously. In order to determine the yaw one free flight photograph was taken of each projectile at a distance of about 50 cm to the target. Table 2.1 provides the experimental data of all the tests.

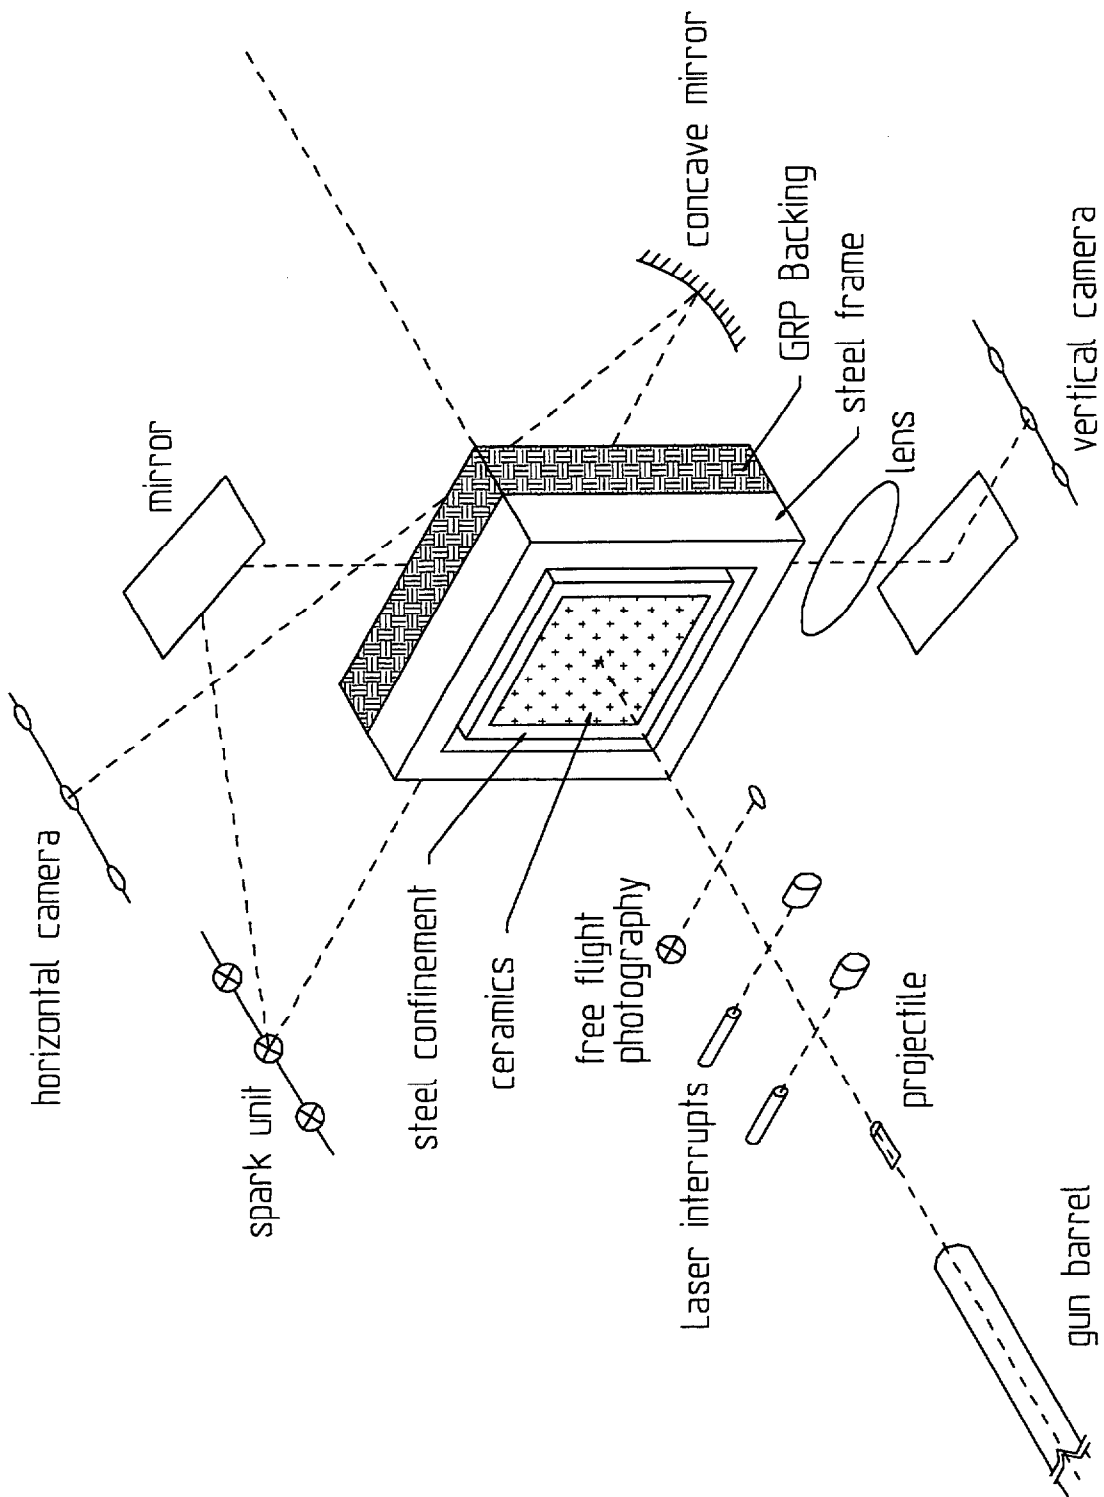


Figure 2.1 Schematic of the experimental configuration

Table 2.1 Experimental data

Shot No.	v_p [m/s]	Target	Yaw
10968	1007	Cer/GRP 24"x24"	0
10997	994	Cer/GRP 24"x24"	2
11000	1091	Cer/GRP 24"x24"	0
10973	991	Cer/GRP 12"x12"	2.3
10994	959	Cer/GRP 12"x12"	4.4
10998	1001	Cer/GRP 12"x12"	3.4
10999	997	Cer/GRP 12"x12"	---

Shot No. 10968

In order to be able to observe the beginning of the bulging the heads of the screws which fixed the GRP panel to the steel frame were countersunk into the GRP. Figure 2.2 shows the complete series of shadowgraphs from the horizontal and the vertical camera. The time intervals were $20\ \mu\text{s}$ between the photographs 1 to 15 and $50\ \mu\text{s}$ between the last 5 photographs. The corresponding distance-time plots of the bulge at the rear side of the GRP panel are shown in Figure 2.3.

The average velocity of the rear of the panel rises up to about 250 m/s and decreases to a few m/s during the first $300\ \mu\text{s}$ after impact. The maximum height of the bulge is 35 mm during the time of observation. A static bulge of 15 mm height remained. Photographs of the target (Figure 2.4) show a delamination in the rear half of the GRP panel. This delamination could possibly be caused by the countersinking of the screws, so that the layers in the rear part of the panel were not pressed together and to the steel frame.

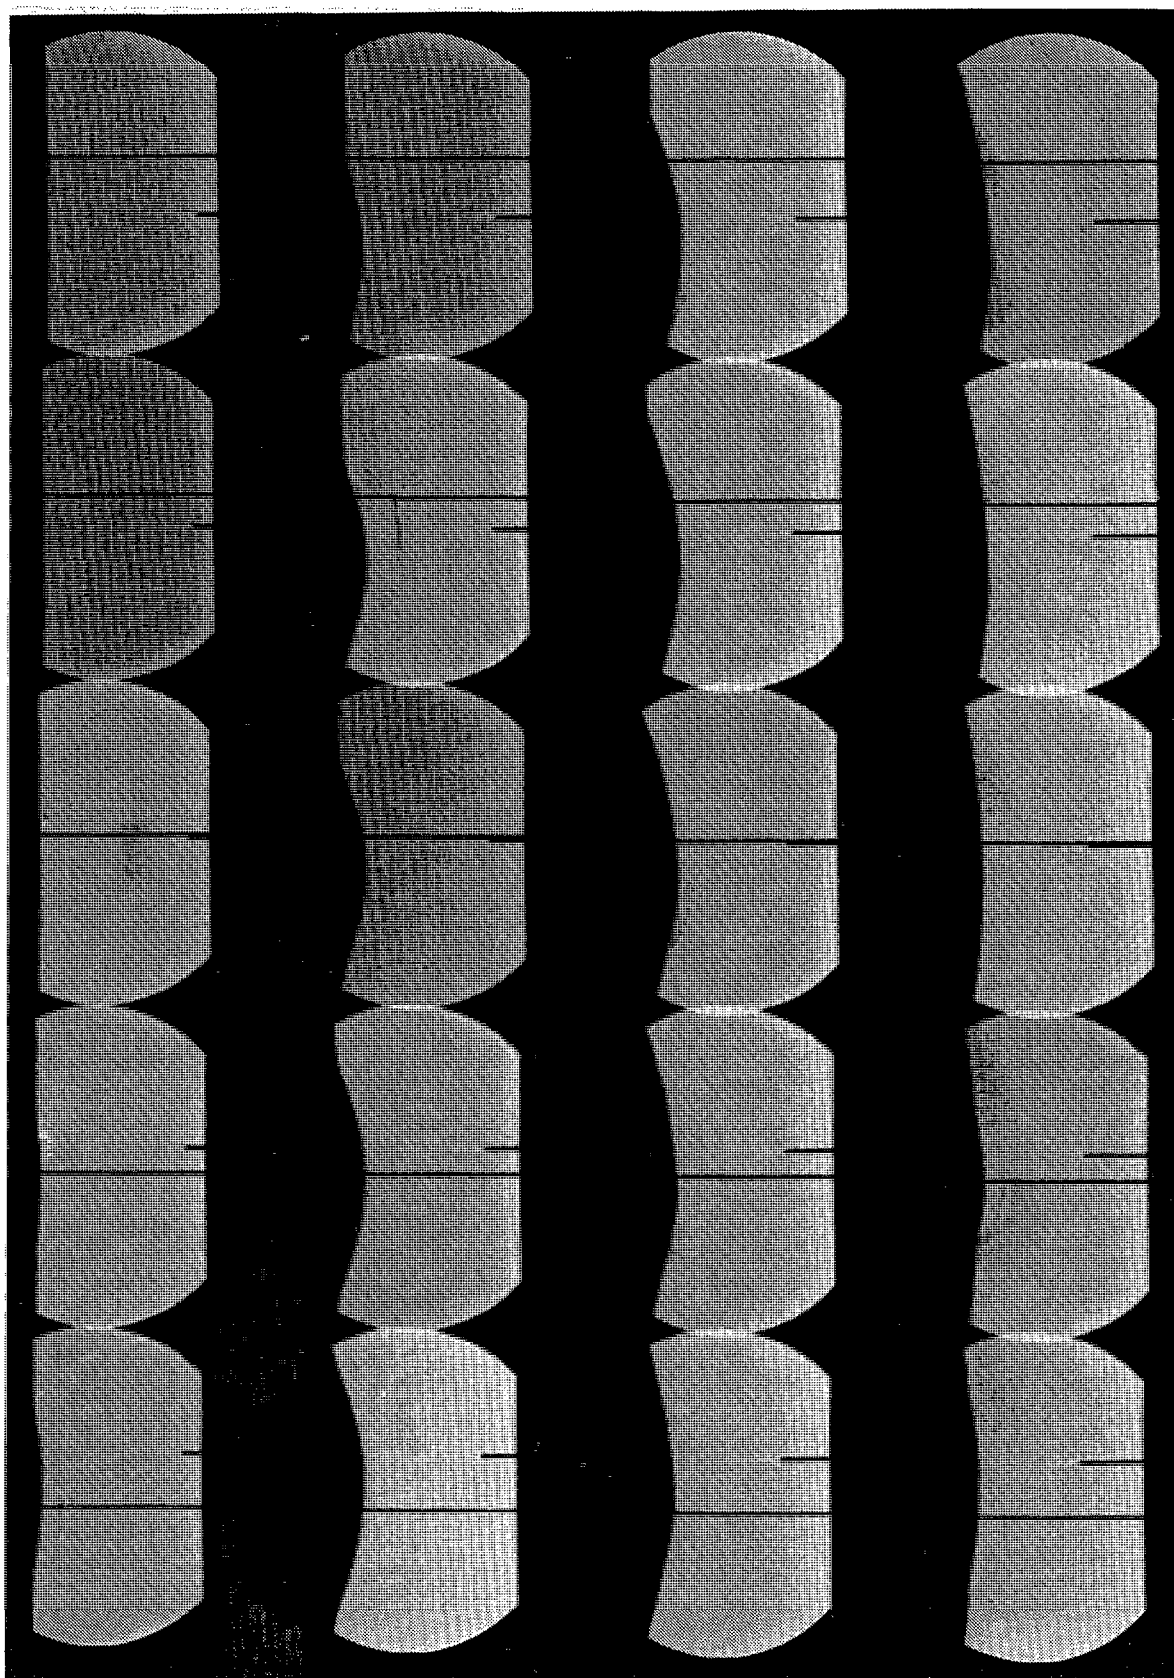


Figure 2.2 Shadowgraphs of Shot No. 10968, side view, $v_p = 1007$ m/s, Cer/GRP 24" x 24", total time $530 \mu s$


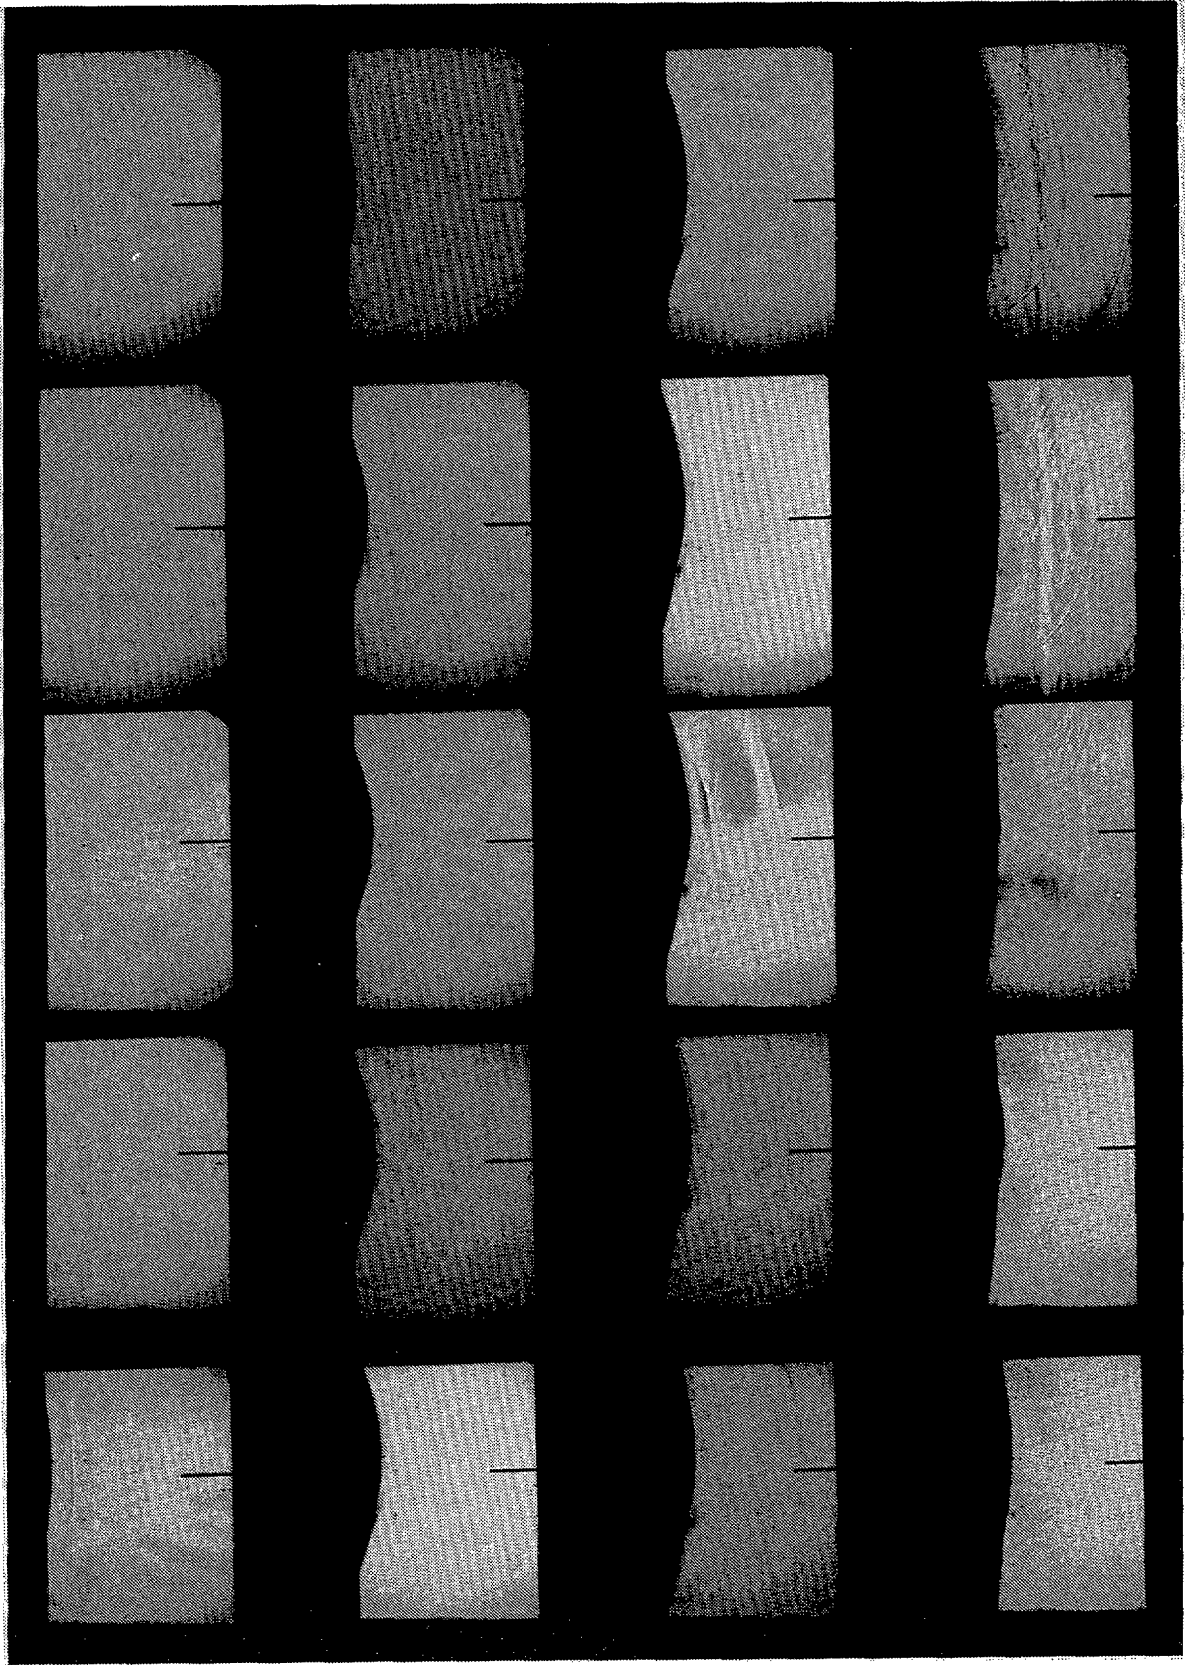


Figure 2.2 Shadowgraphs of Shot No. 10968, top view

Horizontal Camera

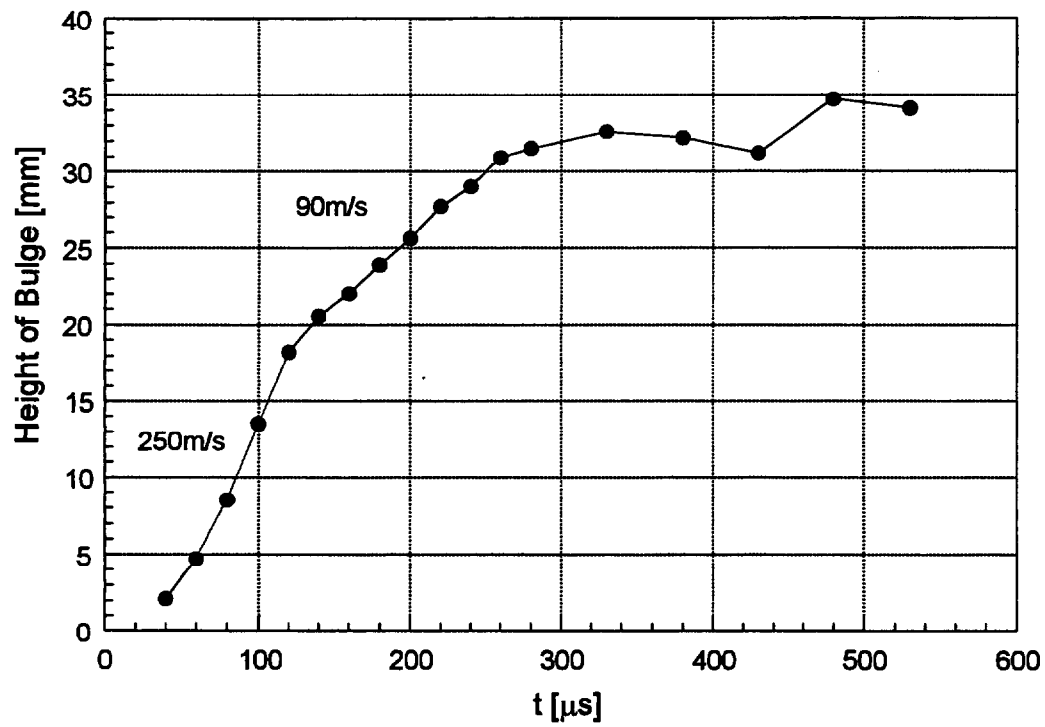

Vertical Camera



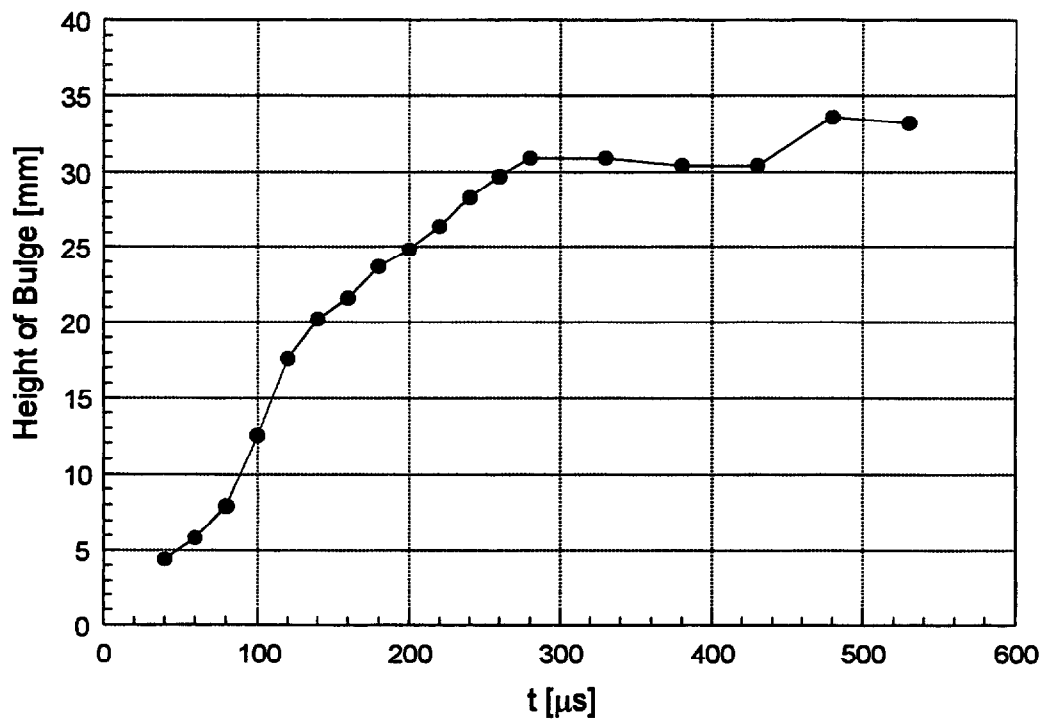


Figure 2.3 Distance-time curves of Shot No. 10968

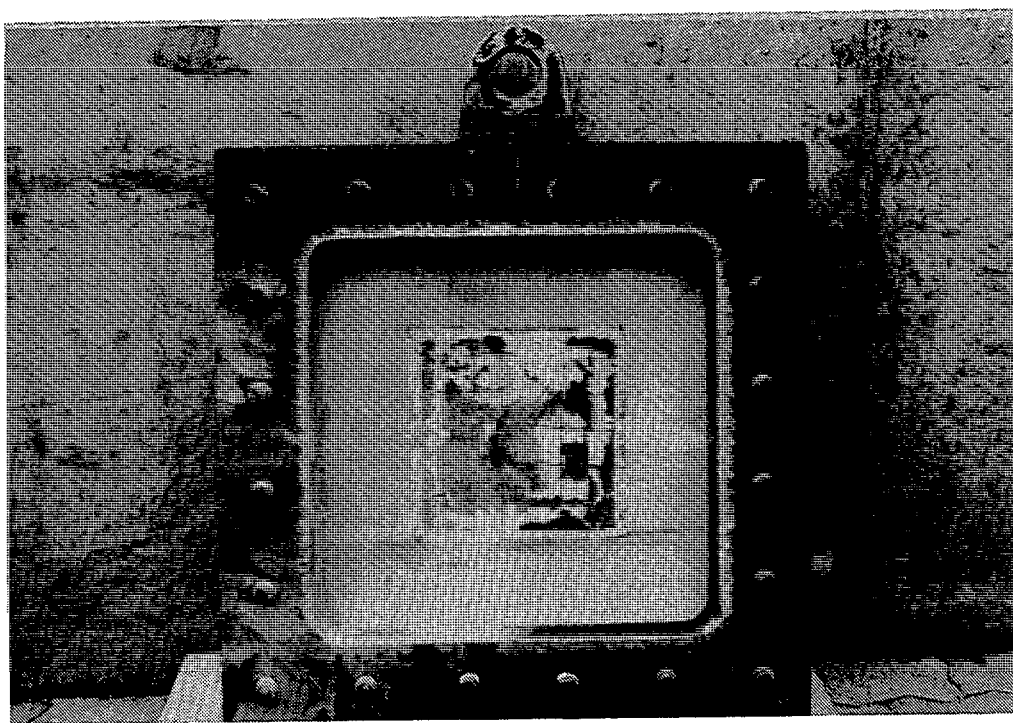

a) Impacted side

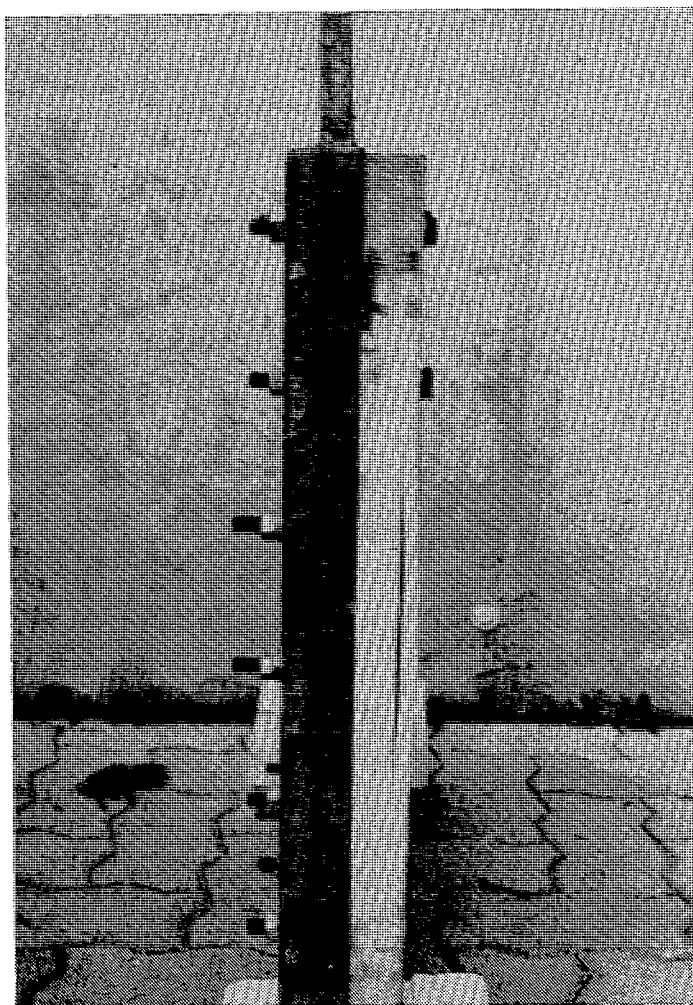

b) Side view, showing the delamination

Figure 2.4 Photographs of the impacted target, Shot No. 10968

Shot No. 10997

In this experiment the GRP panel was clamped to the steel frame in full thickness and bigger washers than in Shot No. 10968 were used. Furthermore, the total time of observation was extended to 1.95 ms. The time intervals between the photographs 1 to 10 were 50 μ s, 100 μ s between photographs 10 to 15, and 200 μ s between the last frames. The series of shadowgraphs are shown in Figure 2.5, the corresponding distance-time plots are provided in Figure 2.6.

The distance-time histories of this shot and Shot No. 10968 are well matched. The bulge reaches its maximum height of 35 mm between 300 μ s and 400 μ s after impact which is also in agreement with the first shot. Between 600 μ s and 700 μ s after impact the bulge begins to decrease. A displacement of 27 mm of the rear of the panel is observed after 1950 μ s. The static bulge that remains has a height of 15 mm. No delamination of the GRP panel is visible from outside which is illustrated by the photographs of the target shown in Figure 2.7. The residual projectile has a mass of 47.7 g and a length of 15 mm.

Shot No. 11000

The first two tests of the 24" x 24" GRP panels yielded a complete path-time history of the bulging process with no failure of the target. Therefore, it was decided to perform the third experiment at a higher impact velocity in order to test the potential protective strength of this target. Figure 2.8 shows the series of shadowgraphs. The time intervals between the photographs were 50 μ s. The corresponding distance-time plot derived from the recording of the vertical camera is shown in Figure 2.9. The shadowgraphs reveal that the projectile perforates the target between 200 μ s and 250 μ s after impact. The blunted nose of the residual projectile seems to be visible in the center of the photographs no. 6 and 7. The residual velocity determined from these two images is \approx 640 m/s. Figure 2.10 shows photographs of the target.

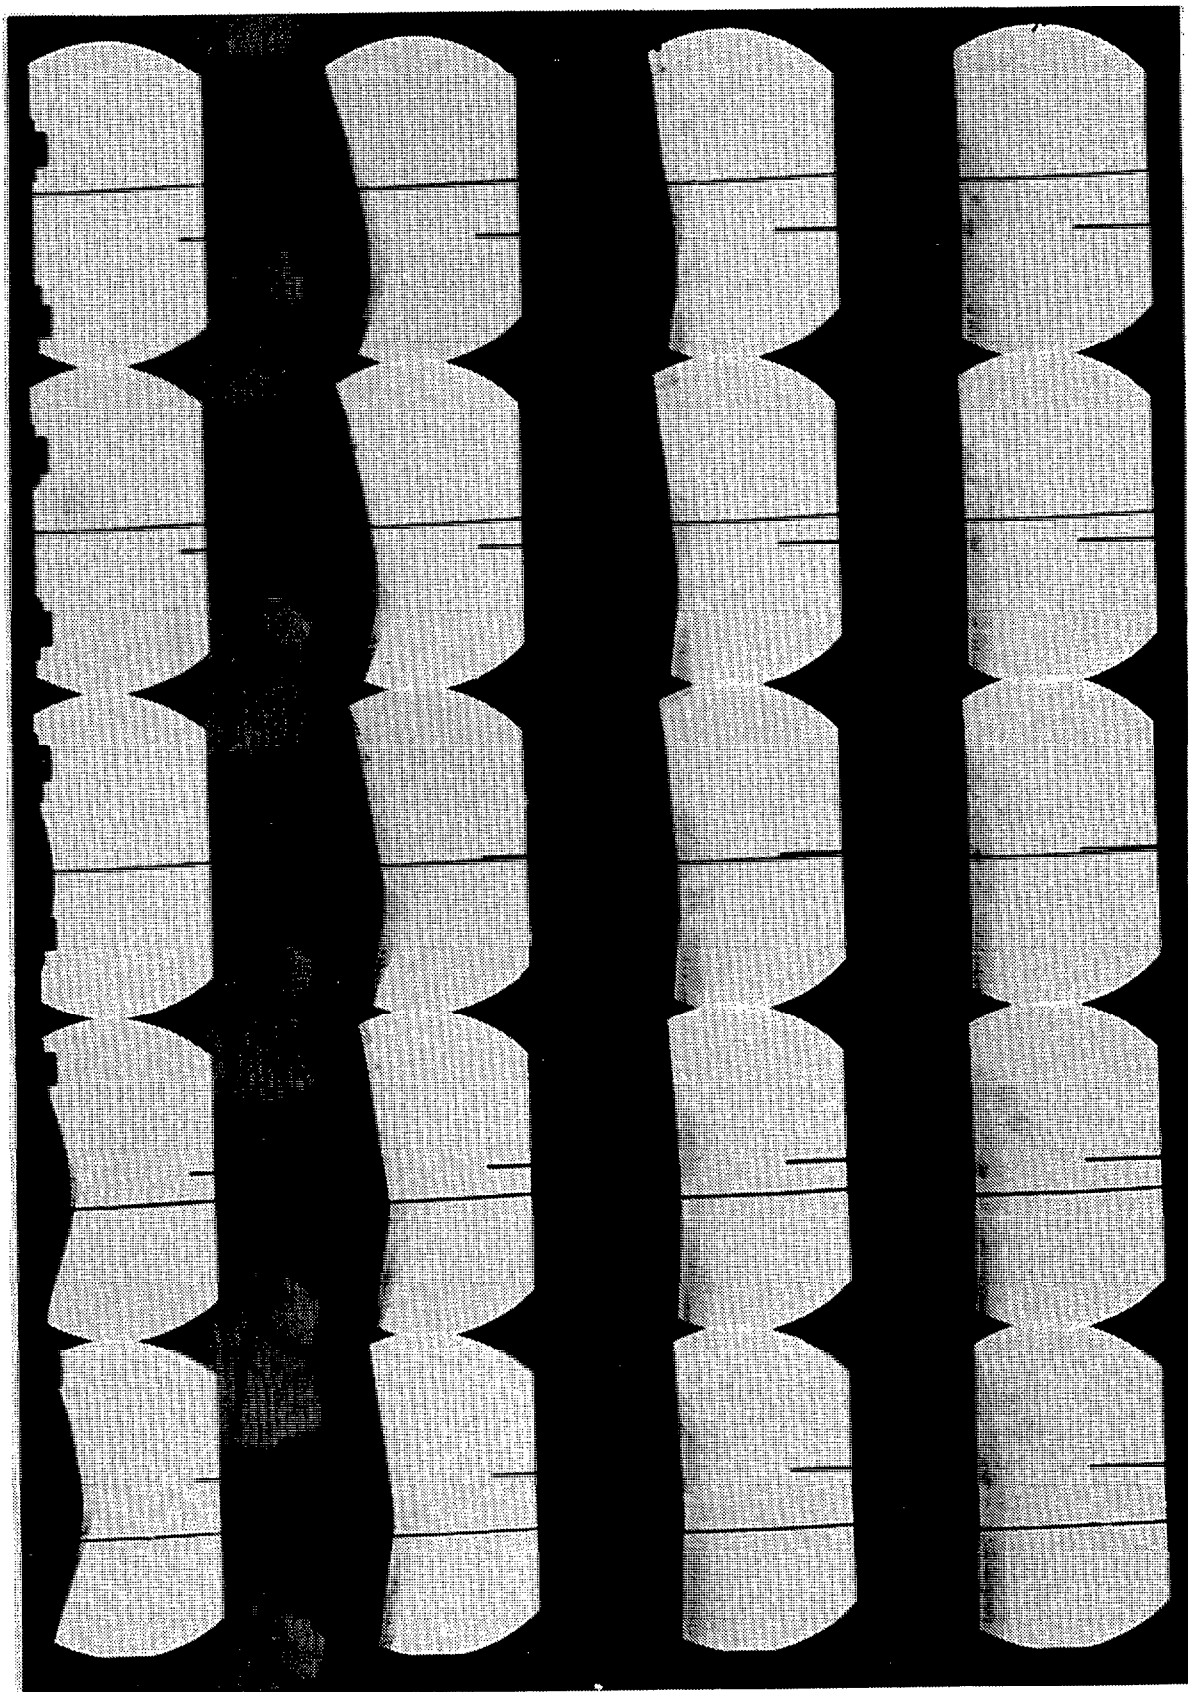


Figure 2.5 Shadowgraphs of Shot No. 10997, side view, $v_p = 994$ m/s, Cer/GRP 24" x 24", total time 1950 μ s

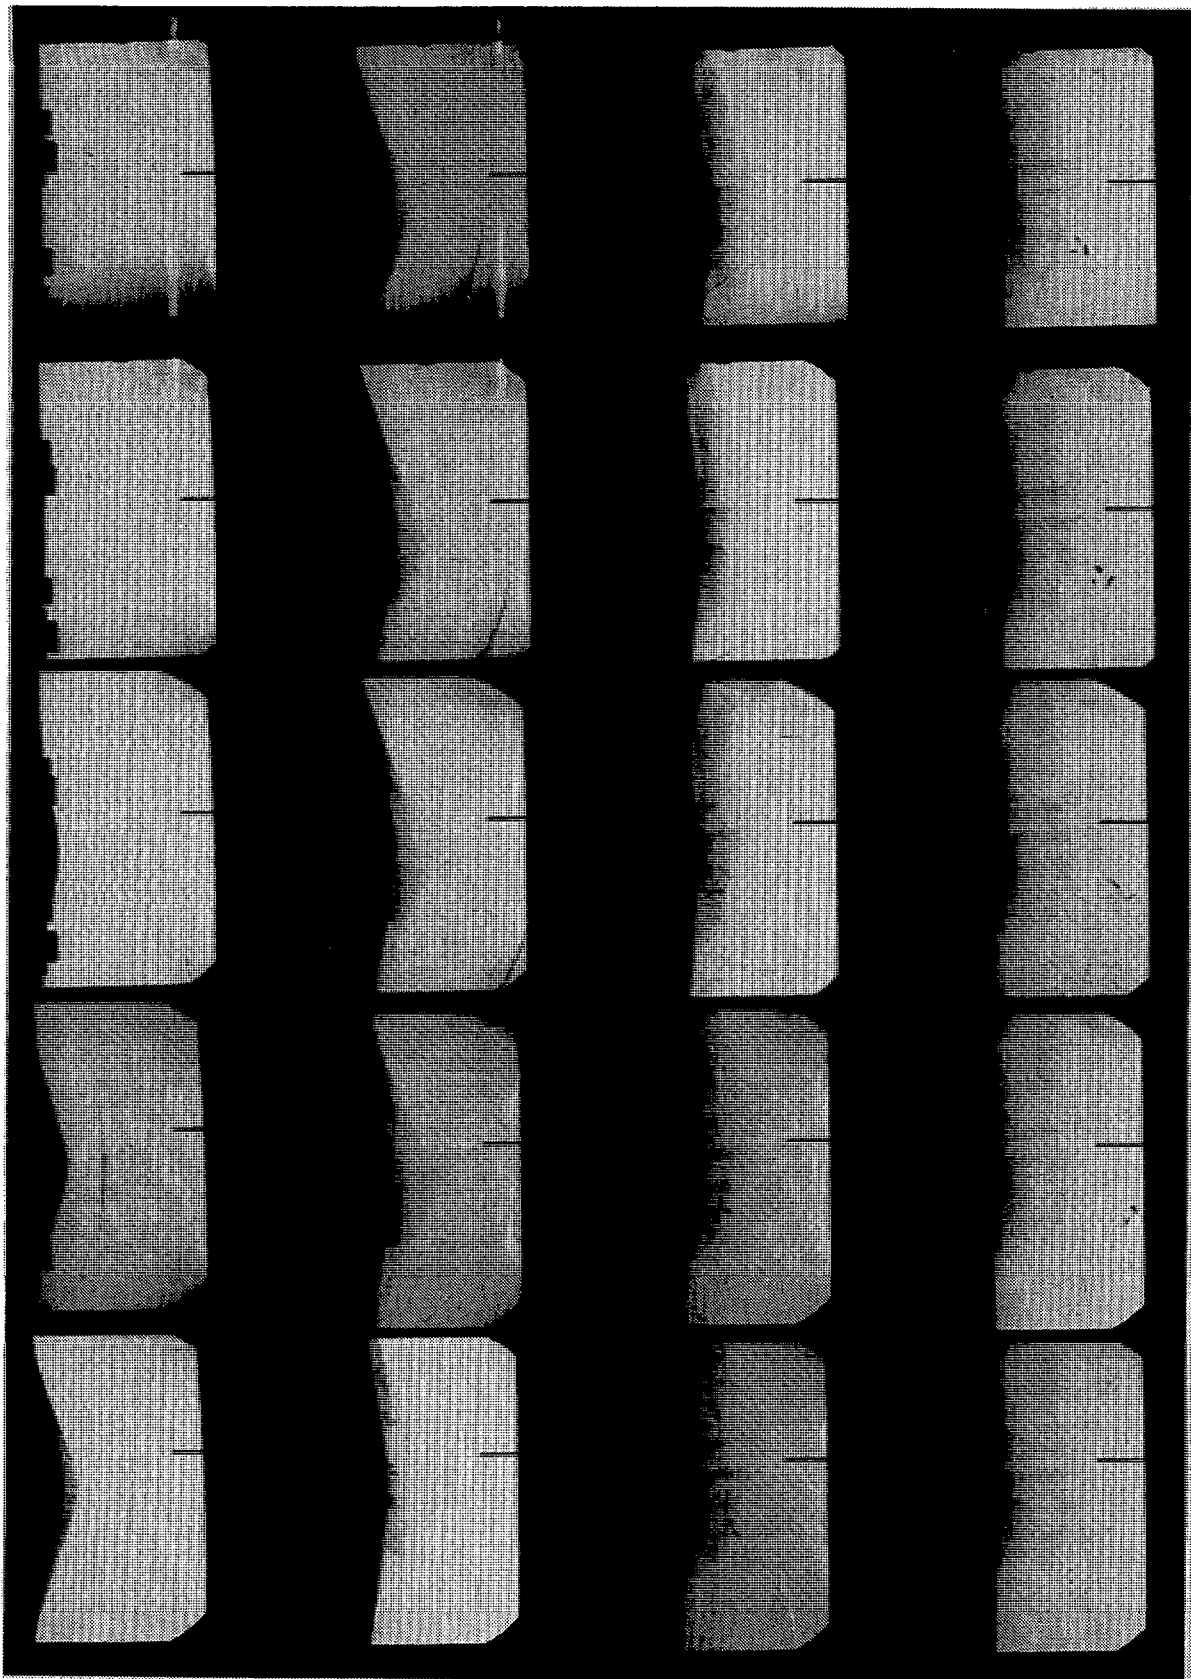


Figure 2.5 Shadowgraphs of Shot No. 10997, top view




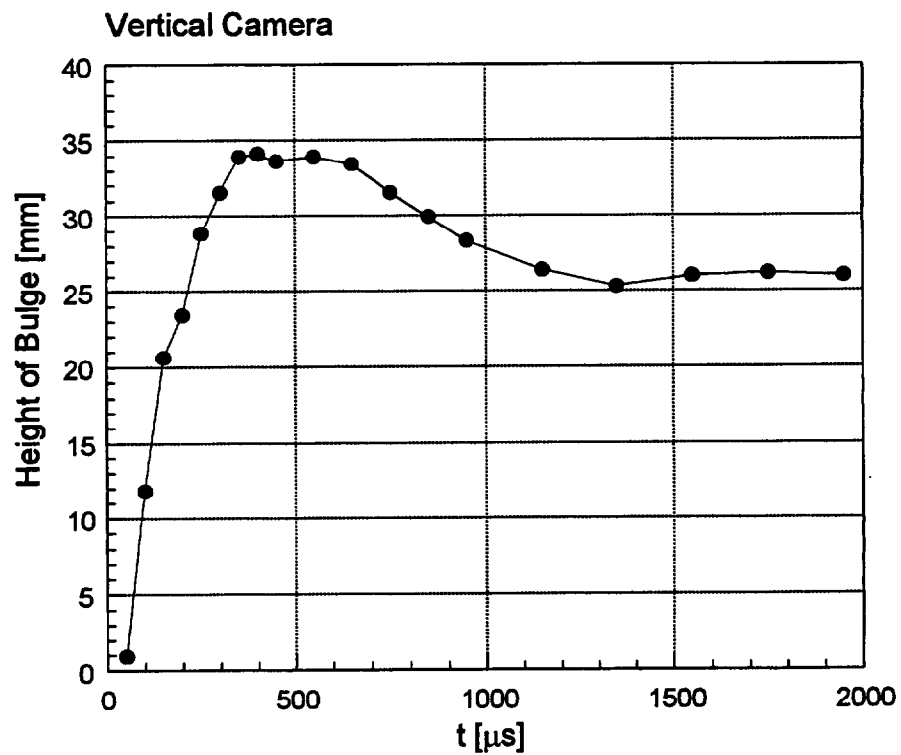


Figure 2.6 Distance-time curves of Shot No. 10997

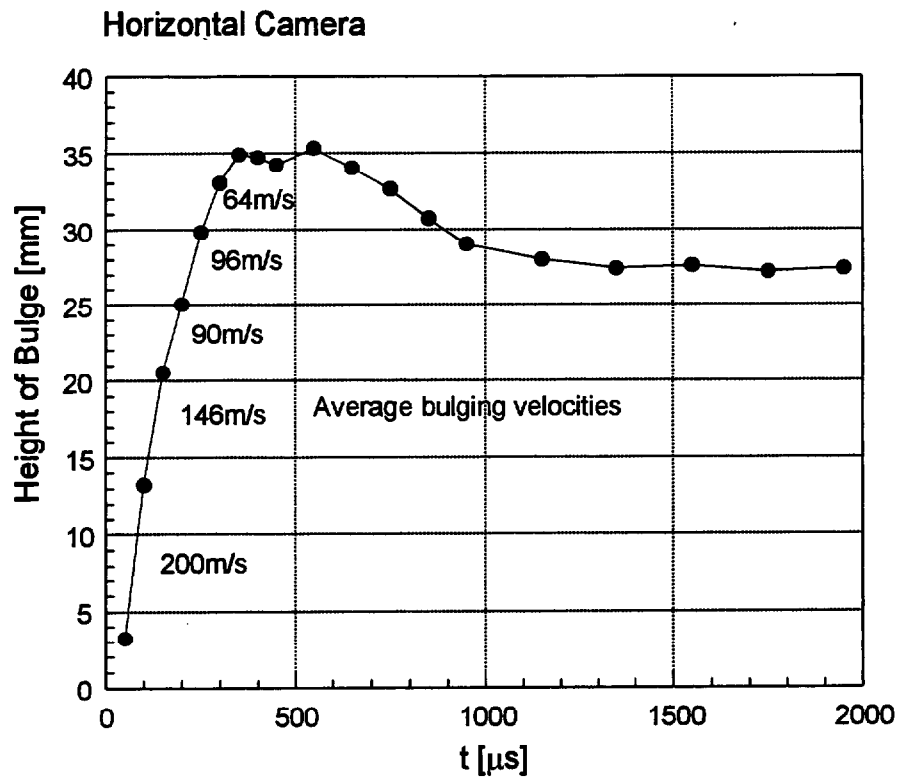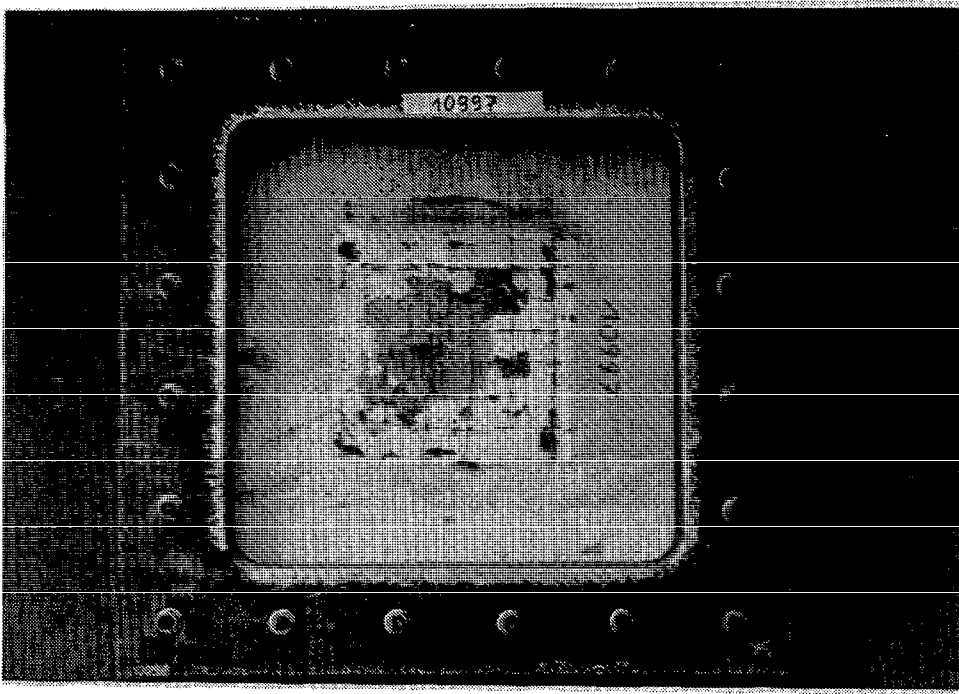


a) Impacted side

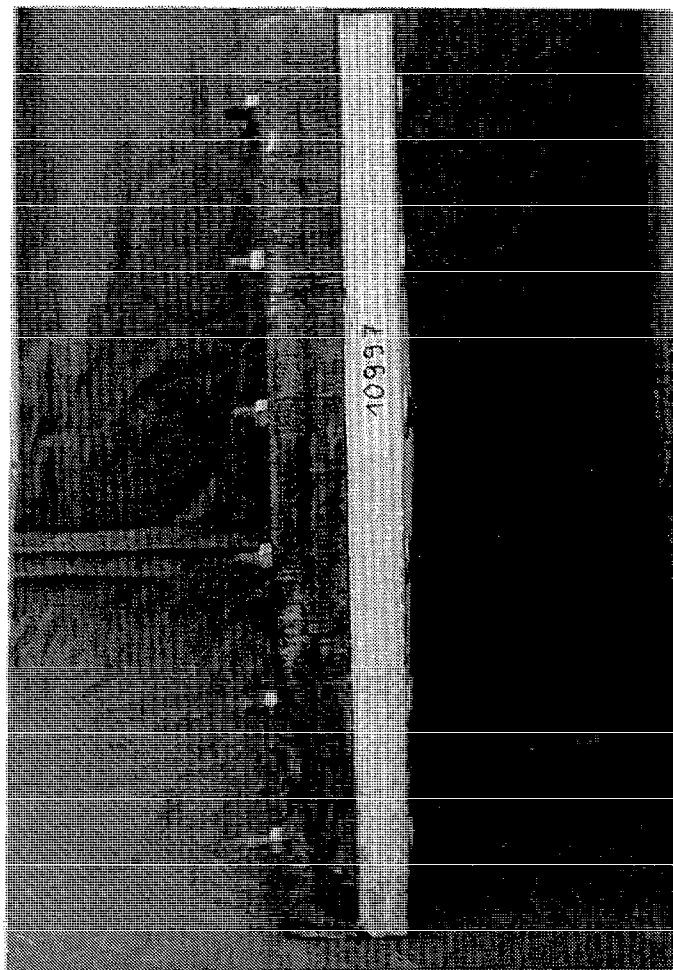

b) Side view, no delamination visible

Figure 2.7 Photographs of the impacted target, Shot No. 10997

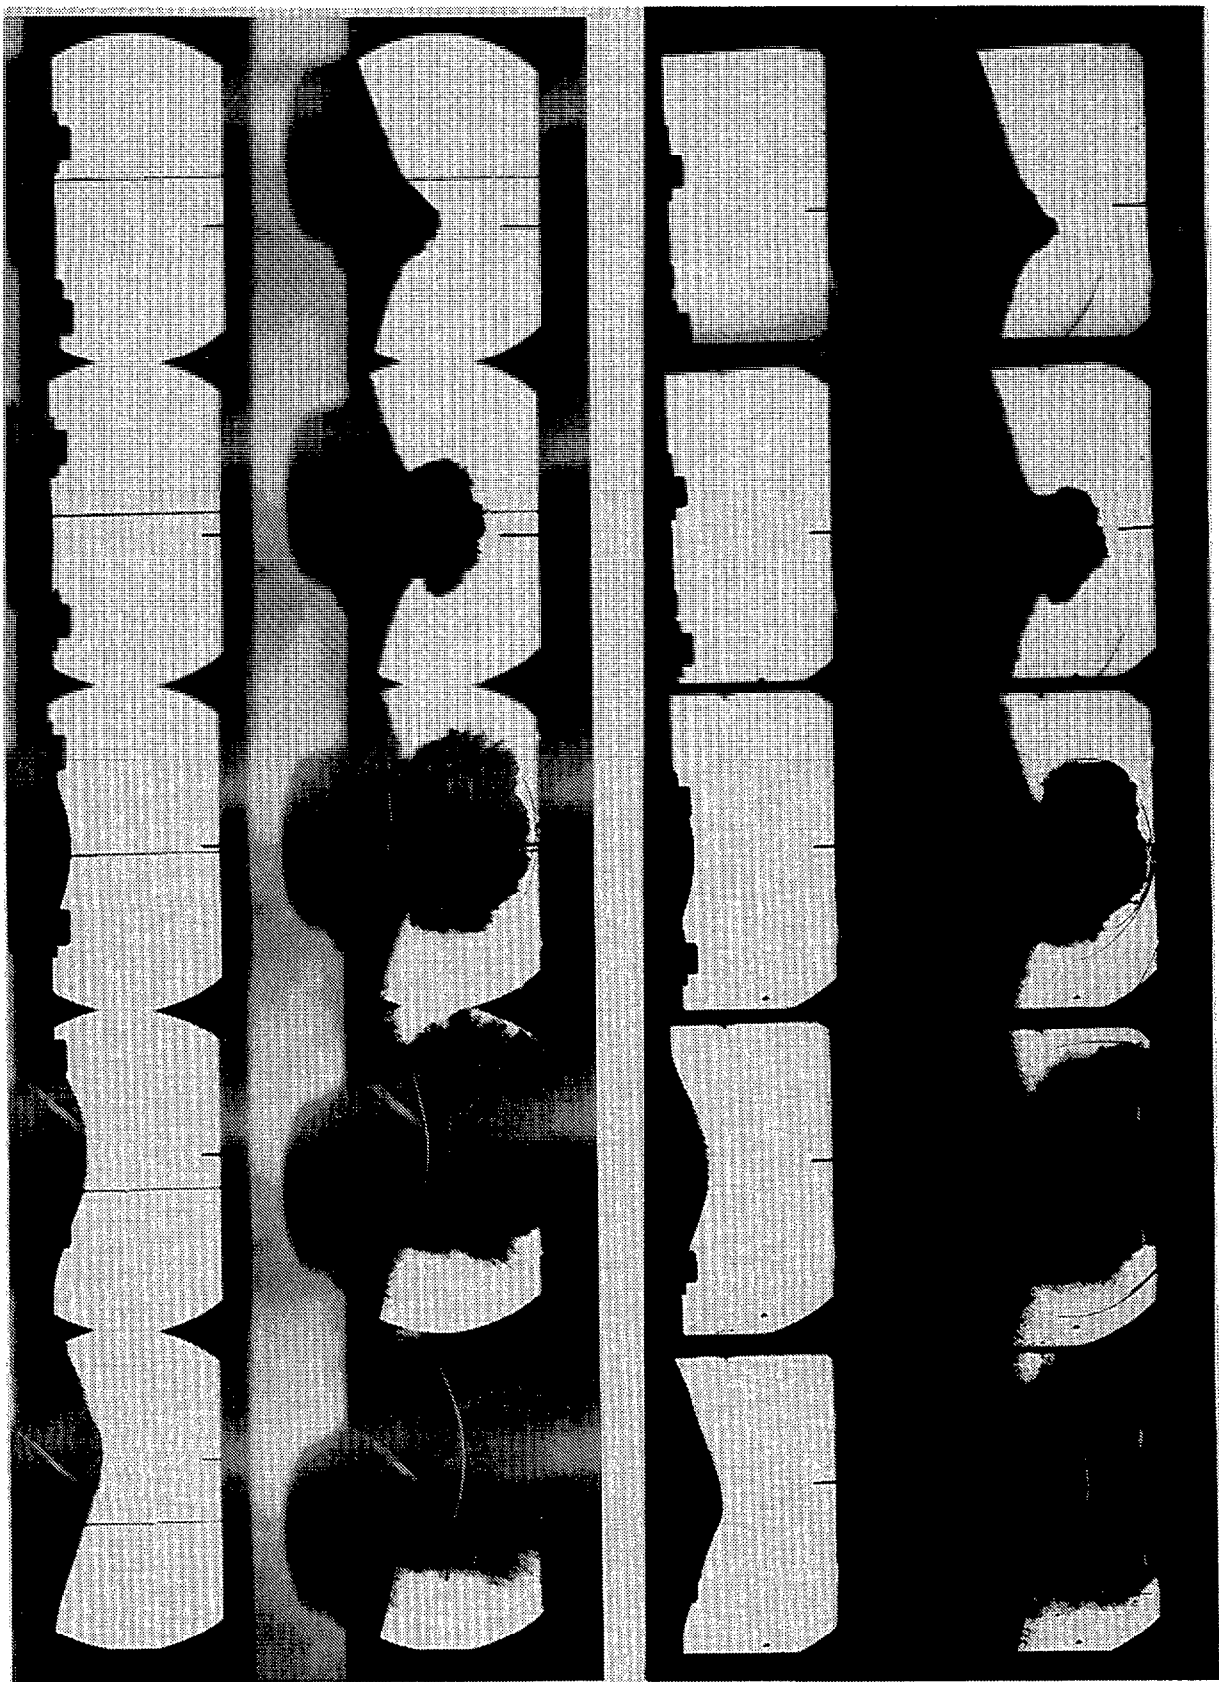

Side view

Top view

Figure 2.8 Shadowgraphs of Shot No. 11000, $v_p = 1091$ m/s,
Cer/GRP 24" x 24"



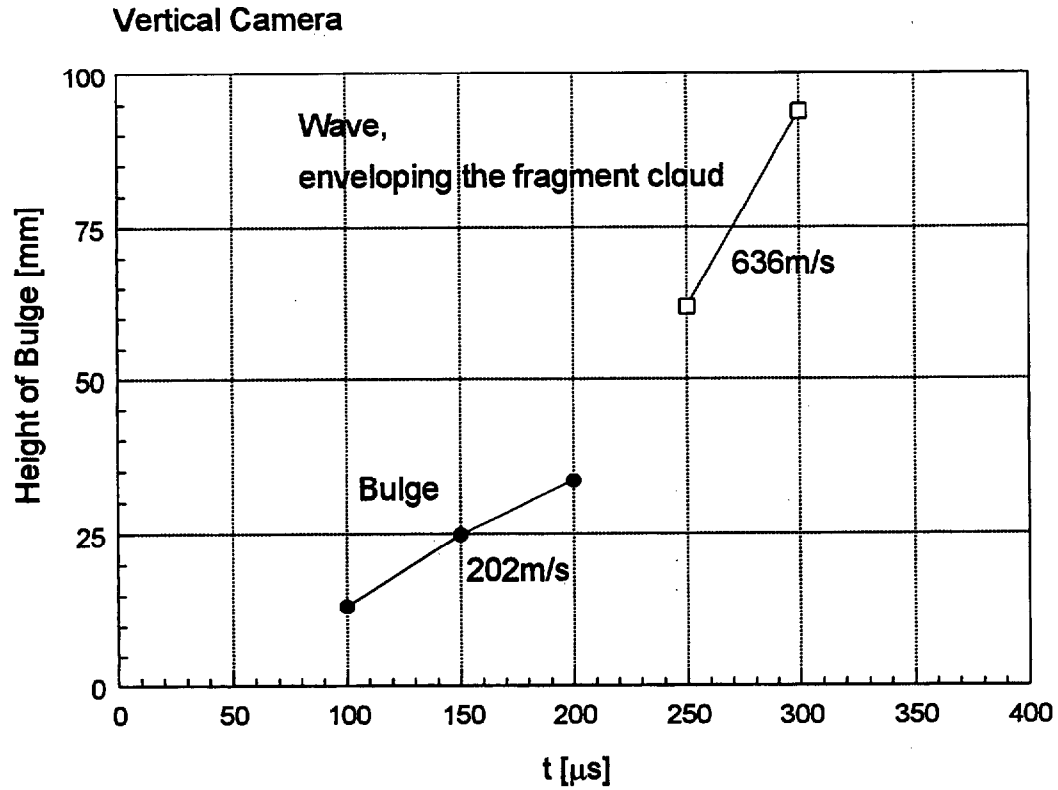


Figure 2.9 Distance-time curve of Shot No. 11000

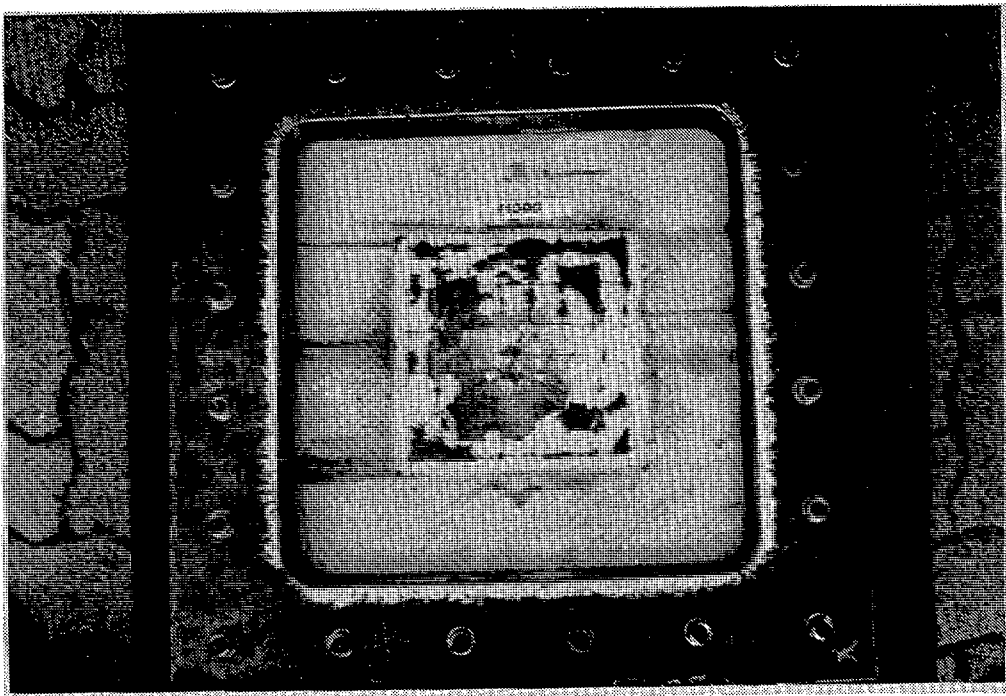

a) Impacted side

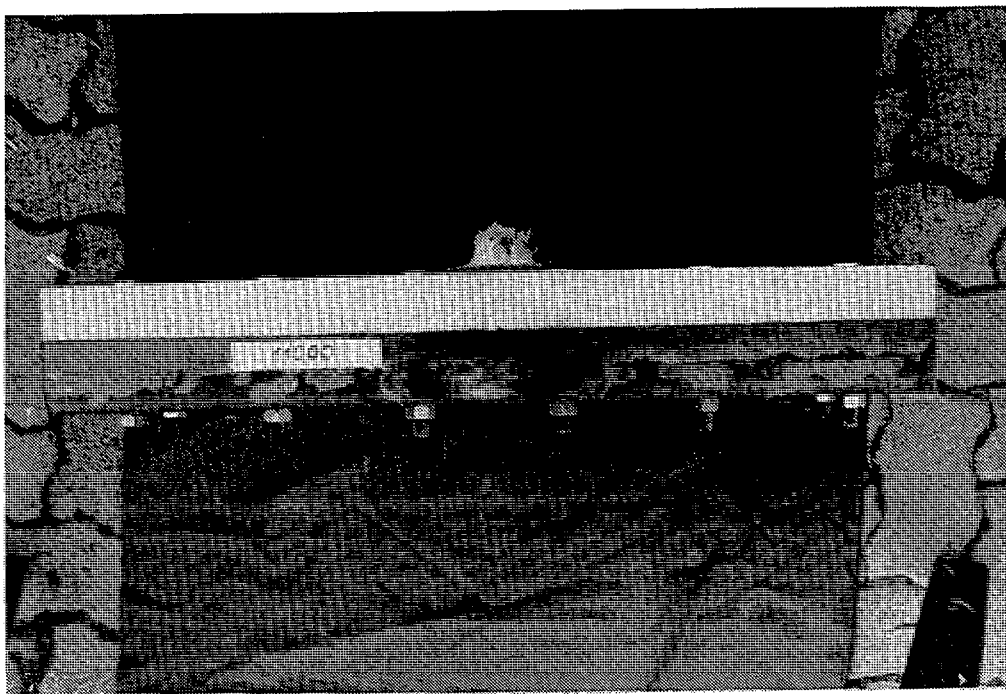

b) Side view

Figure 2.10 Photographs of the impacted target, Shot No. 11000

Shot No. 10973

In the first shot against a 12" x 12" target the heads of the screws were also countersunk into the GRP. The shadowgraphs (Fig. 2.11) show a much stronger bulging in comparison to the 24" x 24" panels. The time intervals were 30 μ s between the photographs 1 to 15 and 60 μ s between the last photographs. A cloud of particles that have been detached from the rear of the small GRP panel can be recognized from picture no. 8. The contour of the cloud, which probably consists of epoxy particles, corresponds to the form of the bulge in an earlier stage.

From the distance-time curves (Fig. 2.12) it can be derived that the average bulging velocity is about 225 m/s during the first 200 μ s and about 90 m/s afterwards. The particle cloud becomes visible approximately at the time when the decrease in the bulging velocity is observed. The inspection of the target revealed that four layers of the glass fiber were completely detached from the rear of the panel. The photographs of the target (Fig. 2.13) show a strong delamination of the GRP panel. Many layers are torn out at the screws or pulled over the washers, which were only slightly bigger than the screw heads.

Shot No. 10994

In the second experiment with a 12" x 12" target the bolts were not countersunk in order to guarantee that the GRP panel was completely fixed to the steel frame. The test was conducted at a striking velocity $v_p = 959$ m/s. Figure 2.14 shows the shadowgraphs which were taken in time intervals of 50 μ s from picture no. 1 to no. 10, 75 μ s from picture no. 10 to no. 15, and 100 μ s between the last pictures. A strong bulging can be recognized which continues during the total time of observation (1325 μ s). The distance-time plots displayed in Figure 2.15 show that the average velocity of the rear of the panel decreases from about 210 m/s to about 40 m/s after more than 1 millisecond. The photographs of the target (Figure 2.16) reveal that the GRP panel was also severely damaged by delamination in the rear half and that many layers were torn around the heads of the bolts. The projectile did not perforate the target. However, the result has to be regarded as target failure.

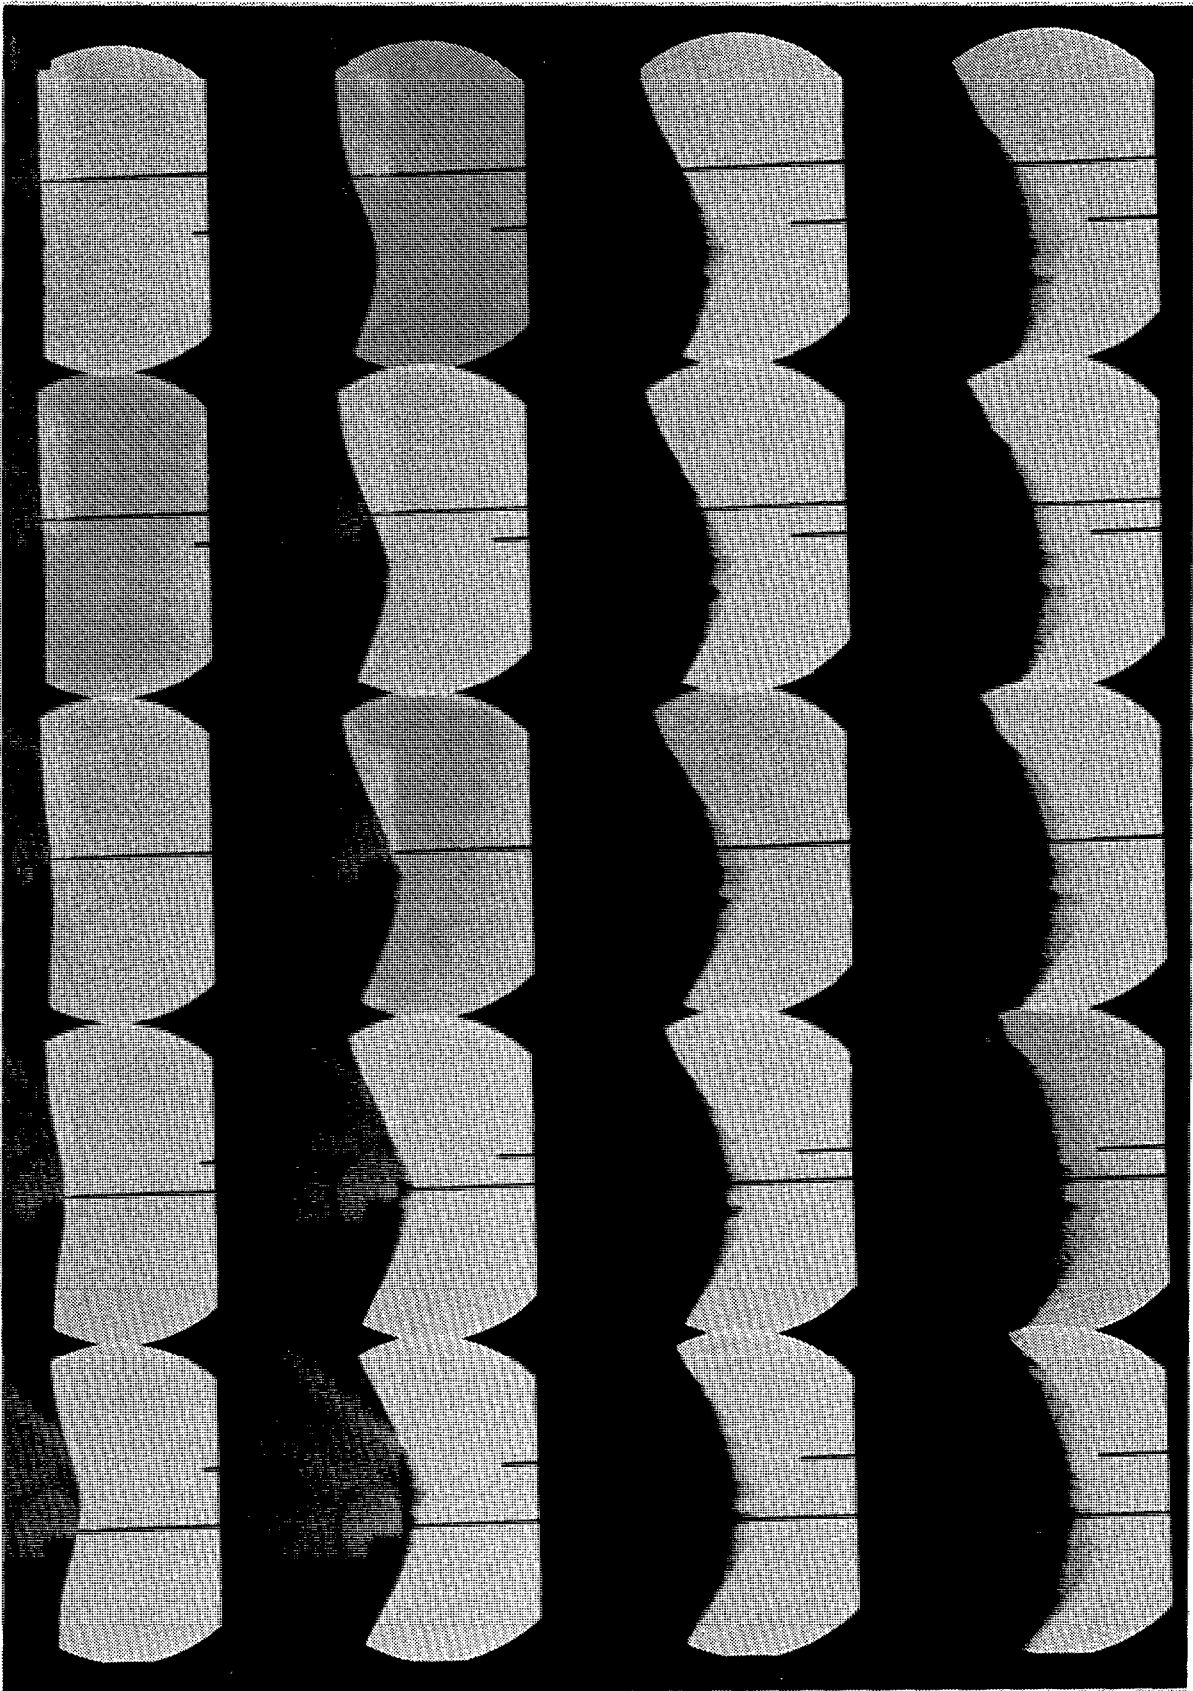


Figure 2.11 Shadowgraphs of Shot No. 10973, side view, $v_p = 991$ m/s, Cer/GRP 12" x 12", total time 730 μ s

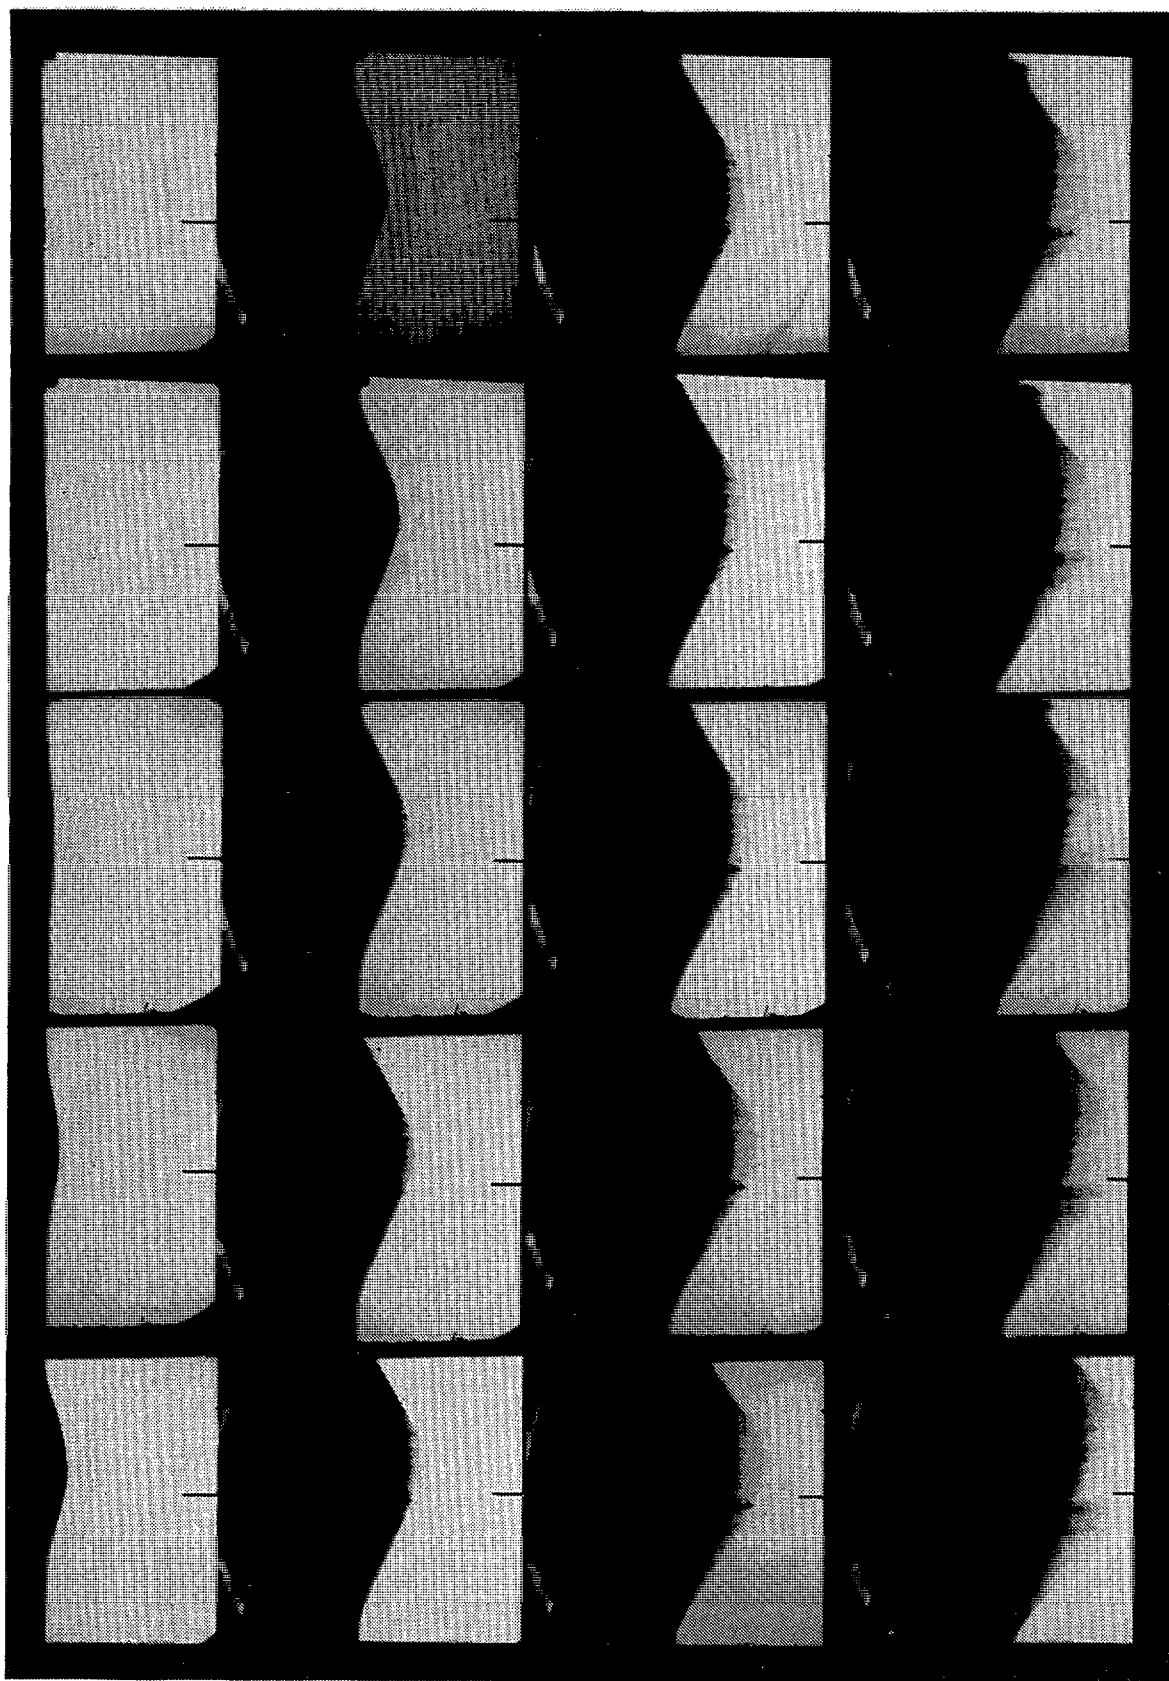


Figure 2.11 Shadowgraphs of Shot No. 10973, top view

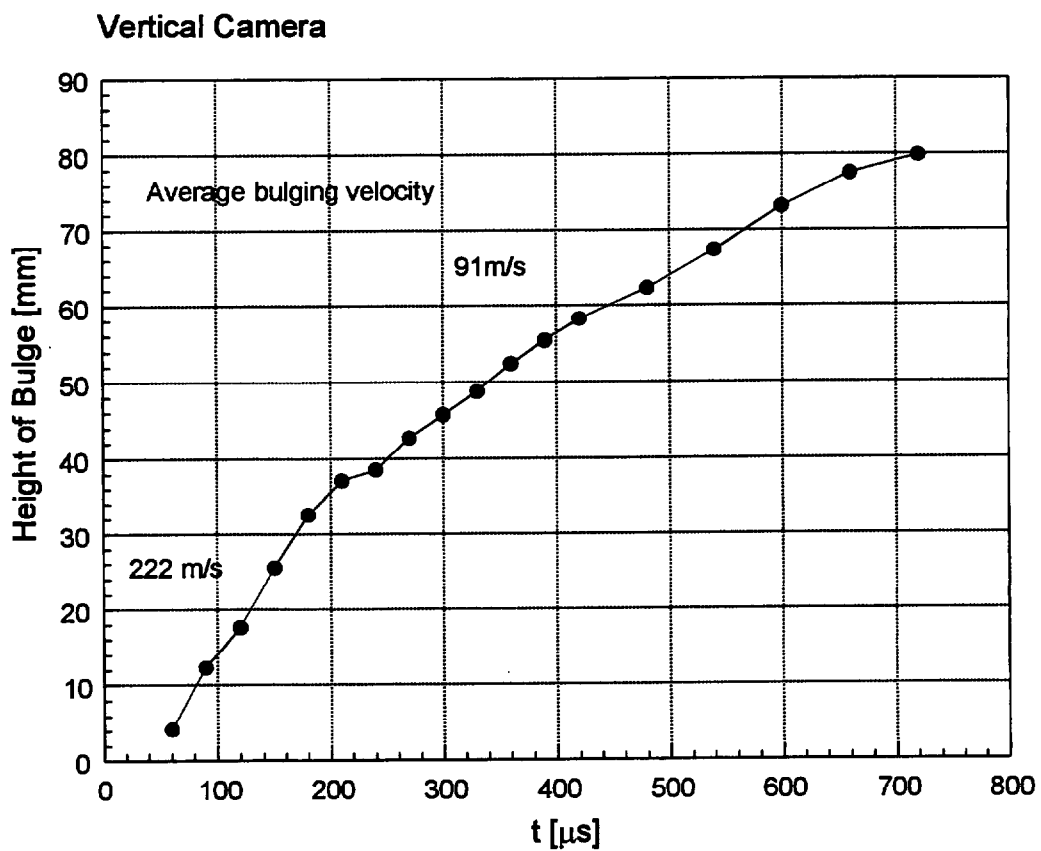
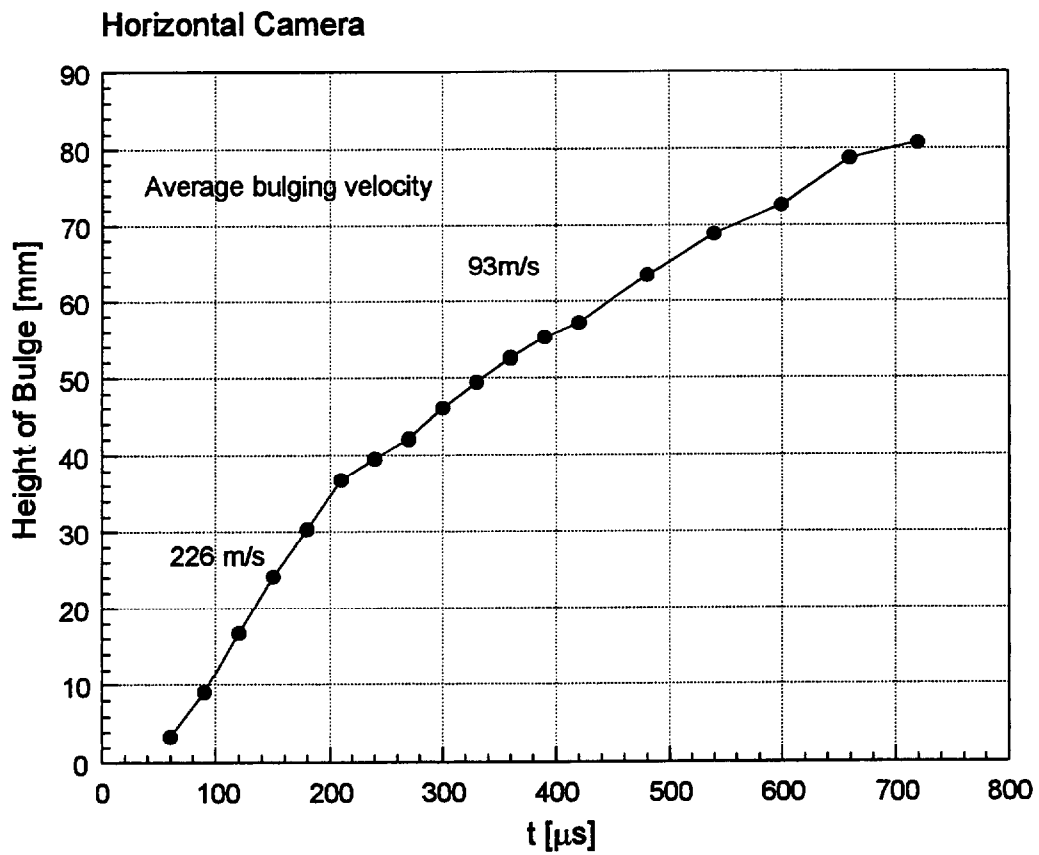


Figure 2.12 Distance-time curves of Shot No. 10973

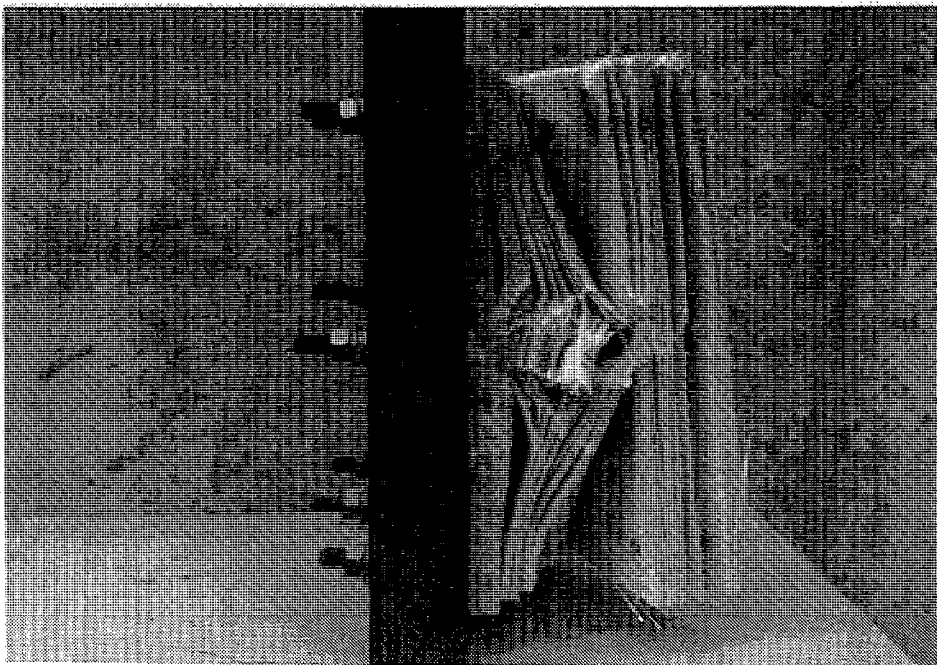
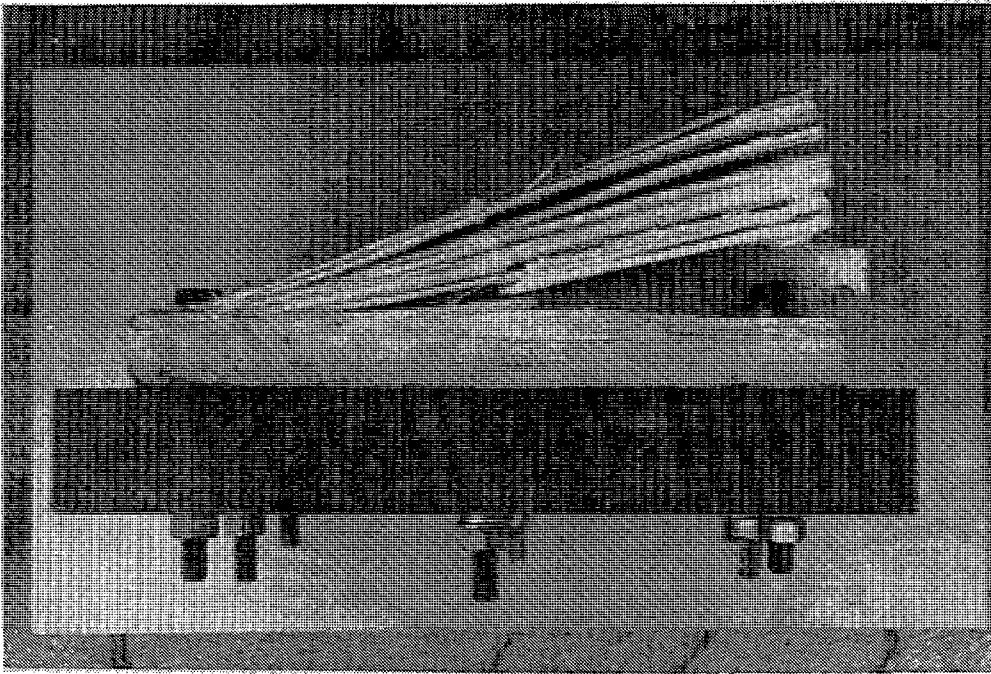


Figure 2.13 Photographs of the impacted target, Shot No. 10973

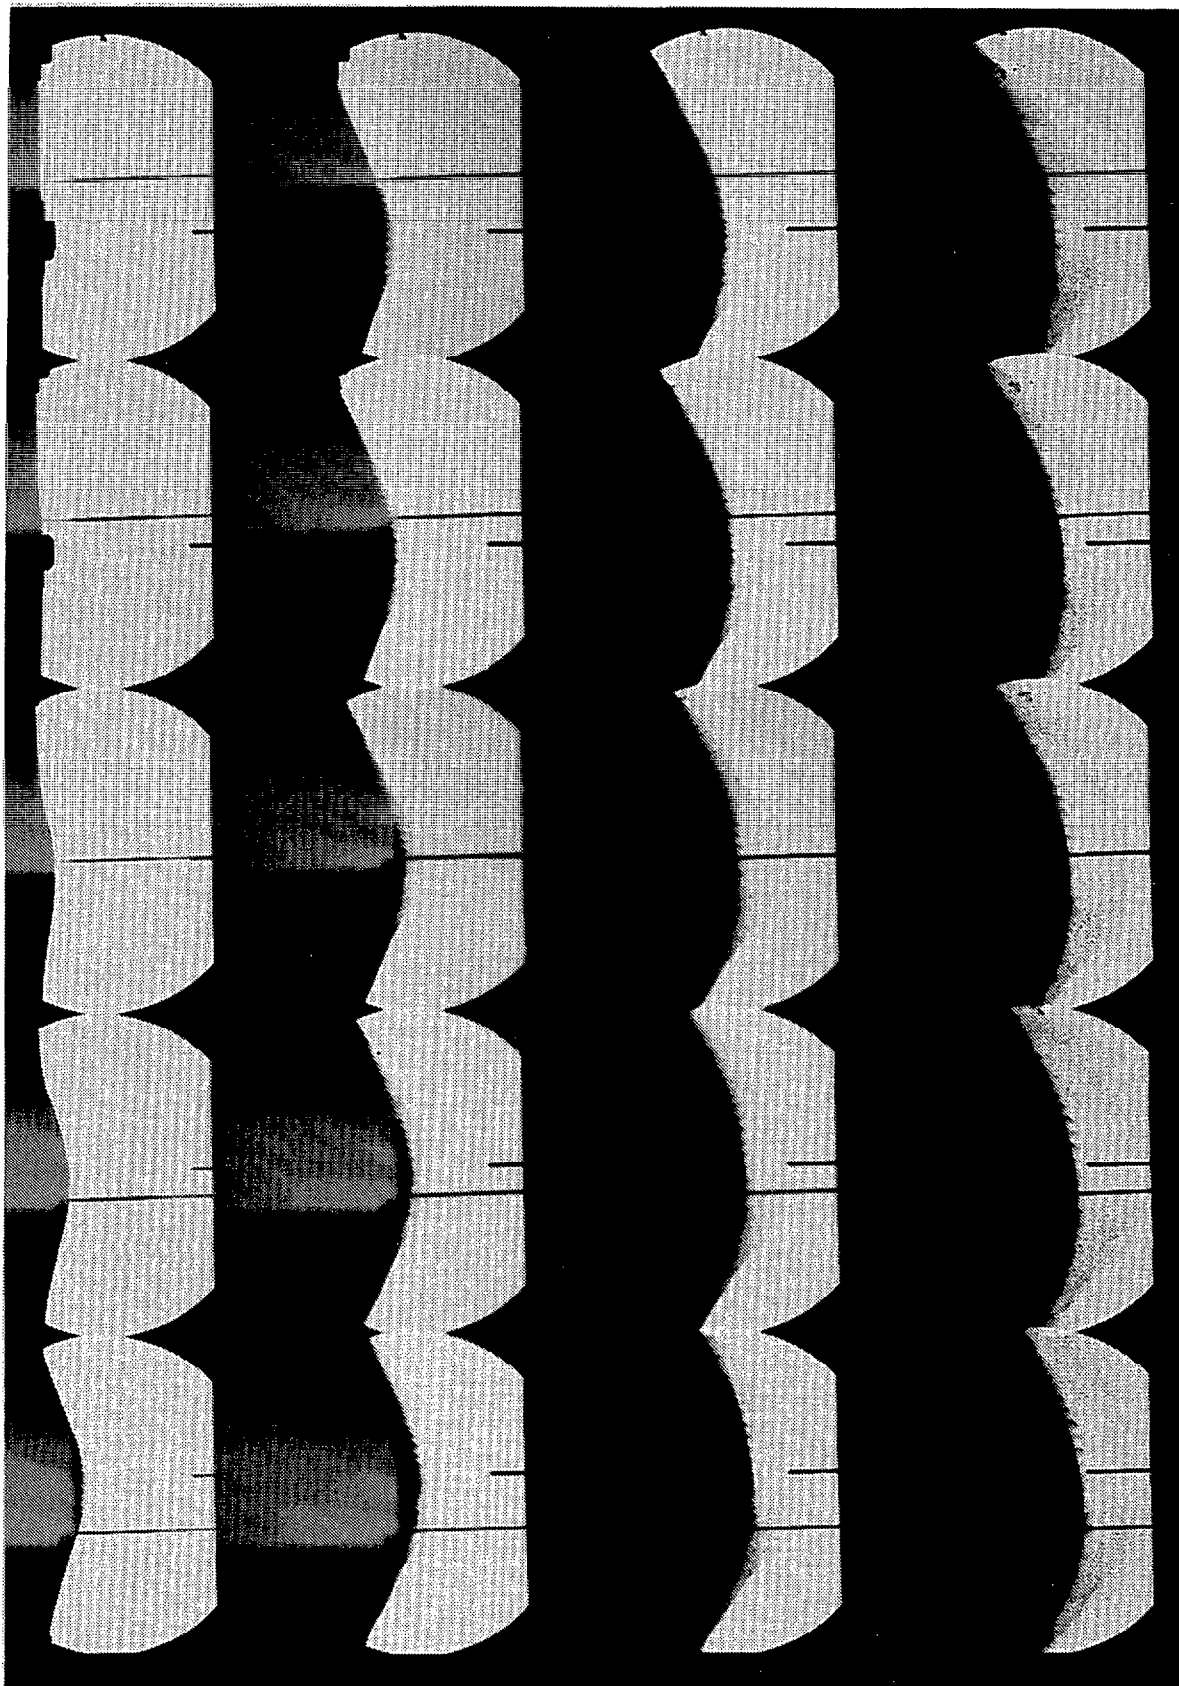


Figure 2.14 Shadowgraphs of Shot No. 10994, side view, $v_p = 959$ m/s, Cer/GRP 12" x 12", total time 1325 μ s

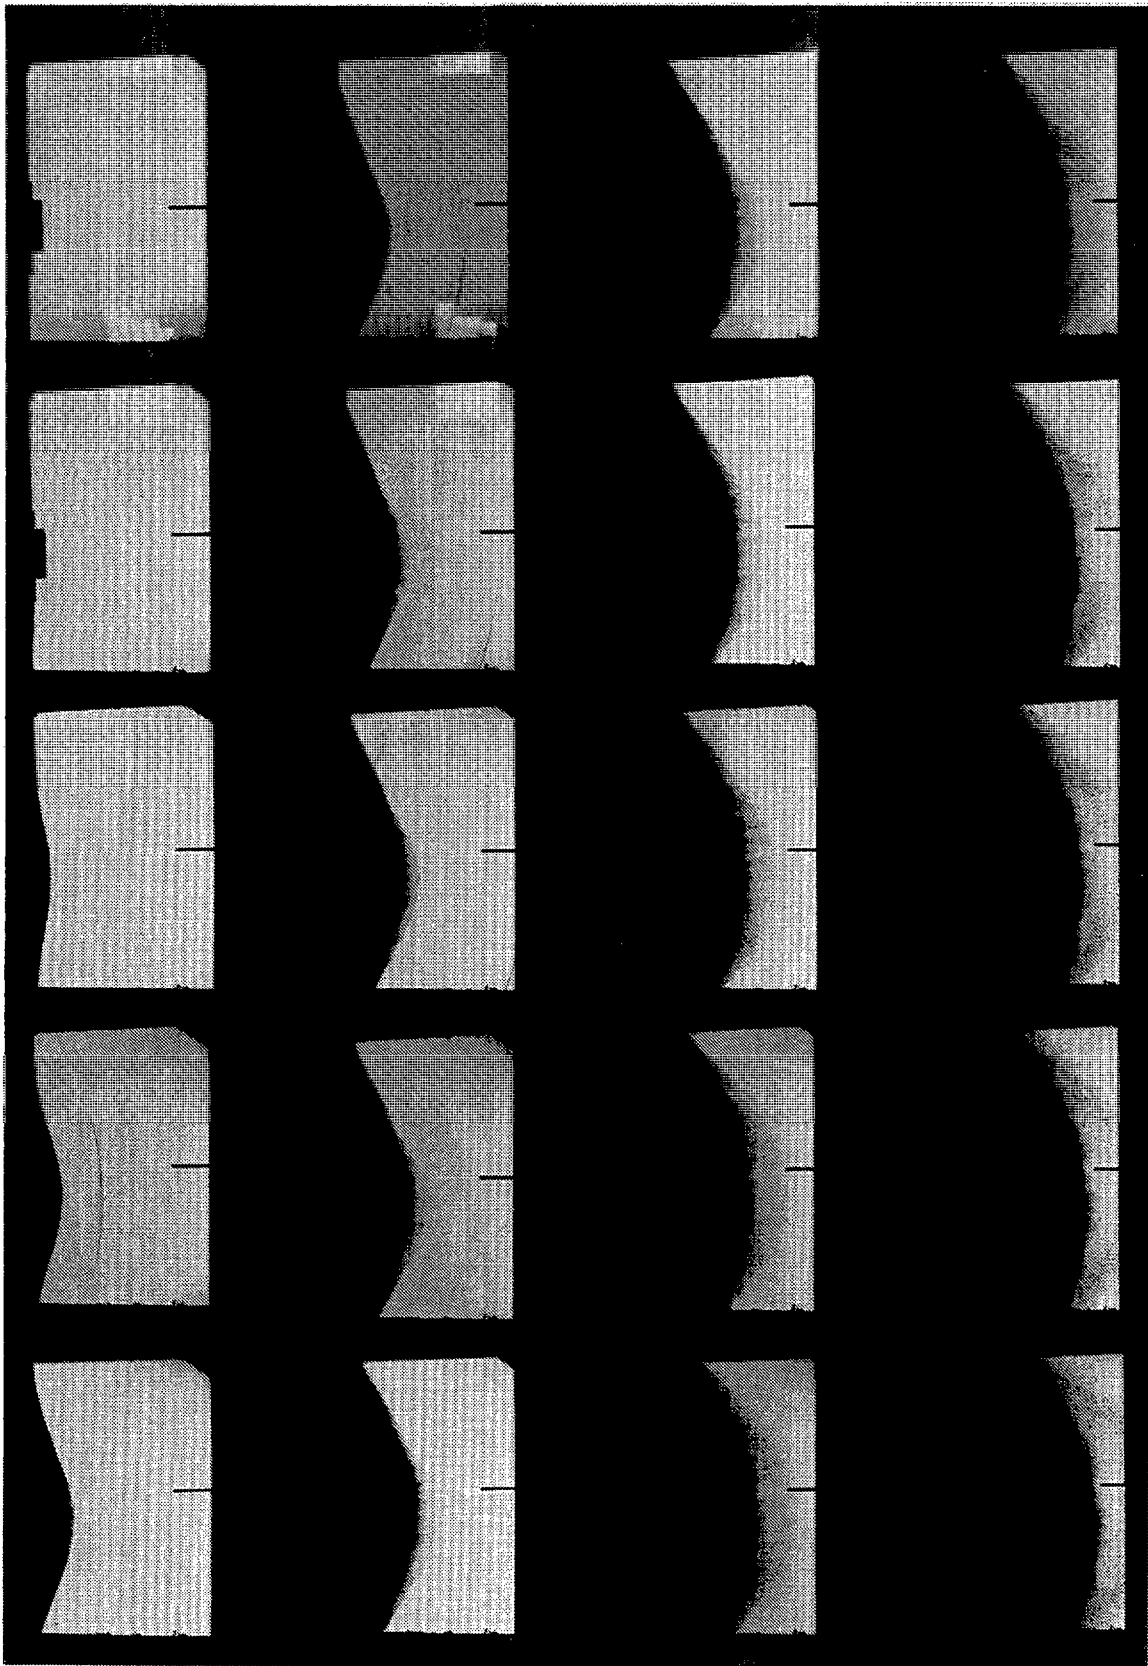


Figure 2.14 Shadowgraphs of Shot No. 10994, top view




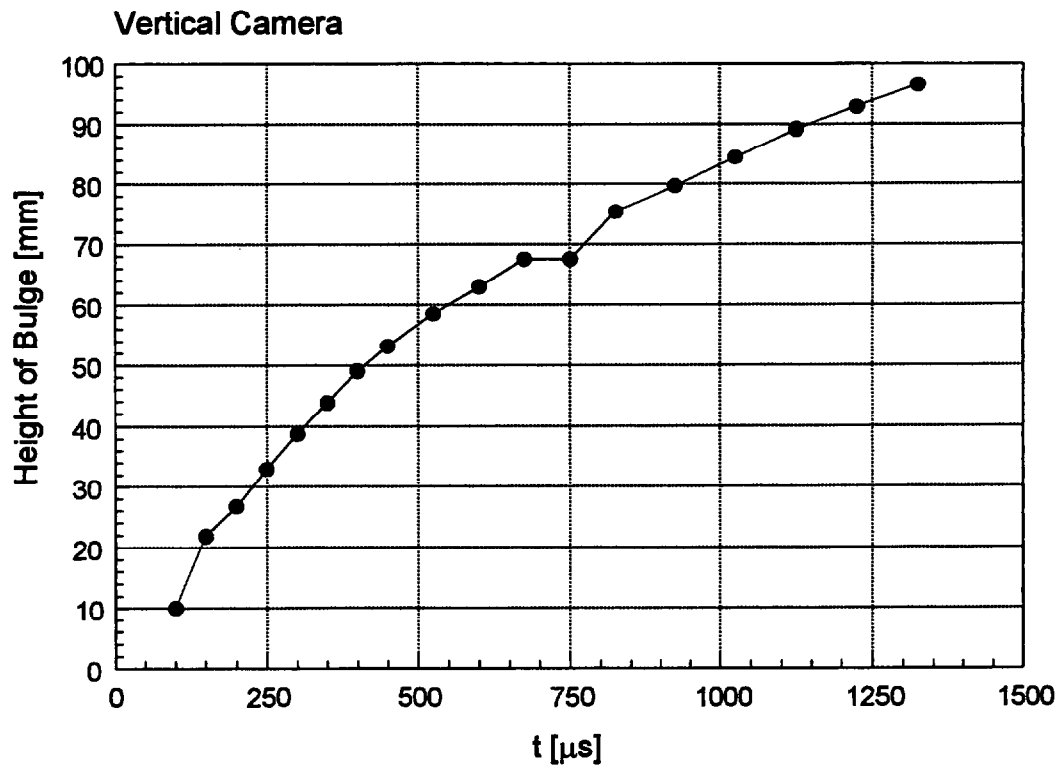


Figure 2.15 Distance-time curves of Shot No. 10994

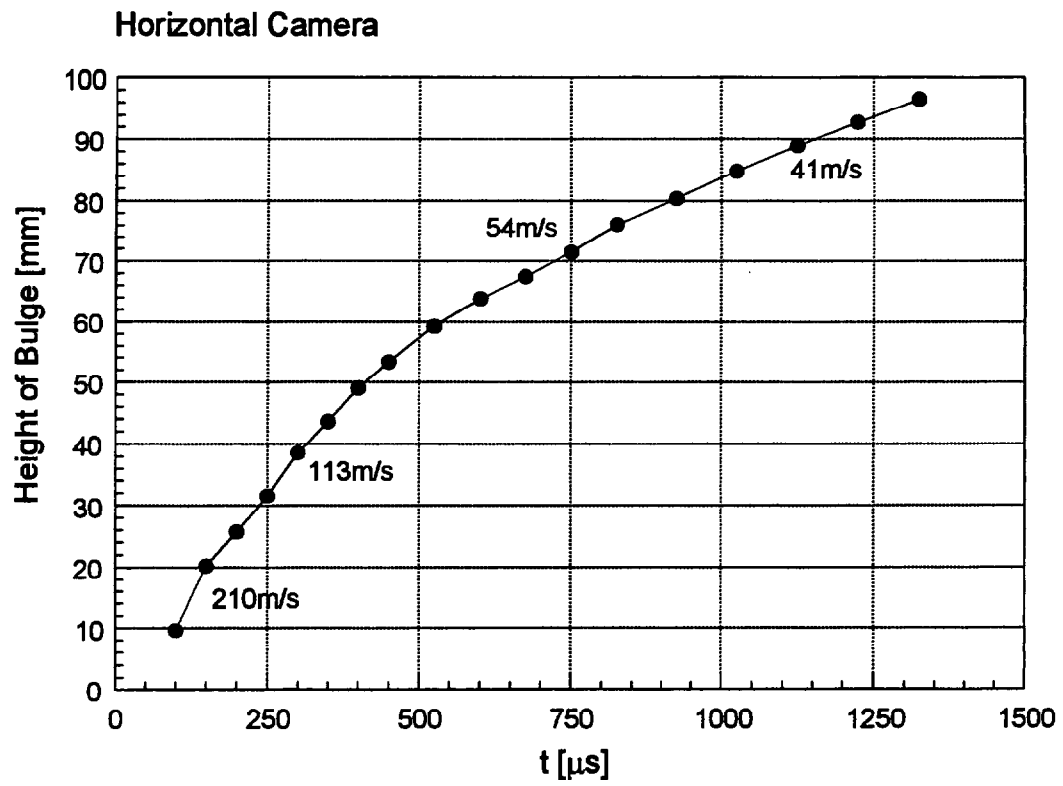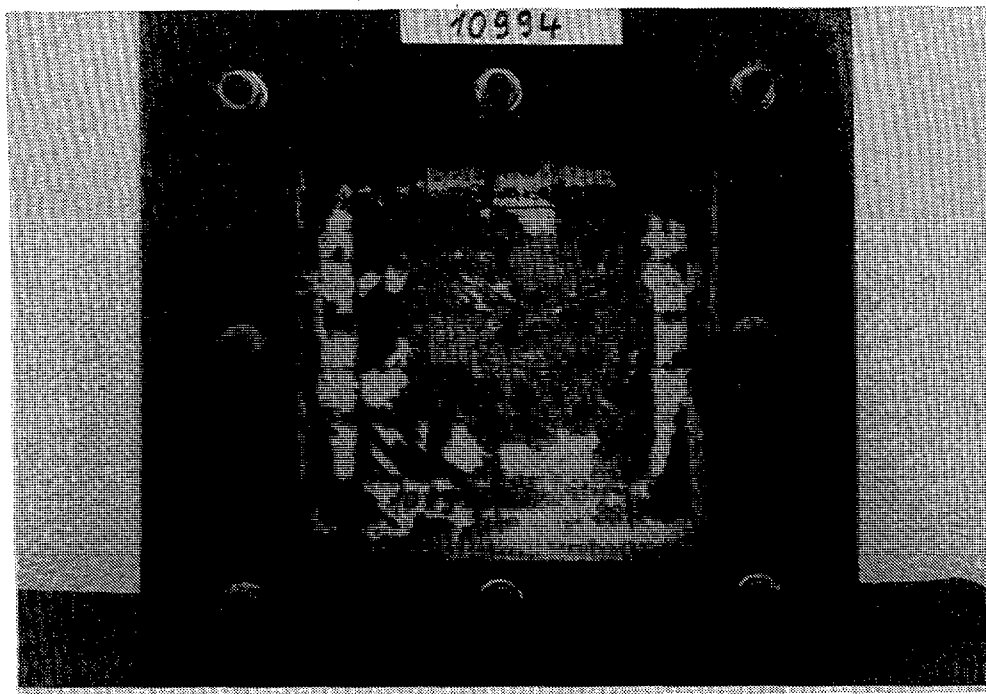

a) Impacted side

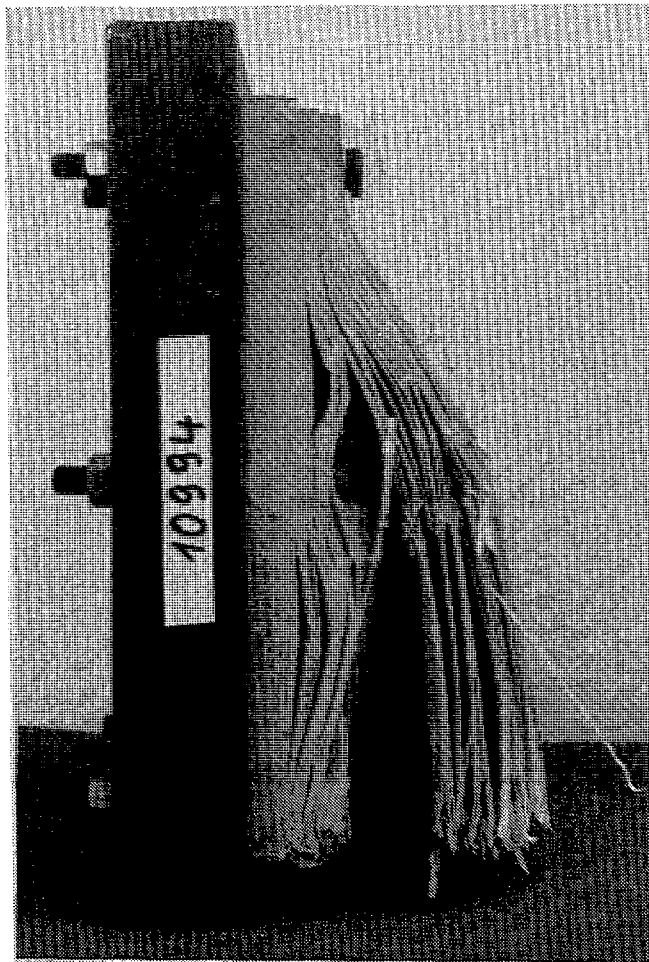

b) Side view, showing the delamination


Figure 2.16 Photographs of the impacted target, Shot No. 10994

Shot No. 10998

In order to prevent GRP layers from being pulled over the nuts a steel frame of 10 mm thickness and 50 mm width was additionally clamped to the rear of the GRP panel. The test was conducted at $v_p = 1001$ m/s. From the shadowgraphs (Figure 2.17) it can be recognized that the projectile perforated the target. The time intervals between the first ten photographs were $50 \mu\text{s}$. Perforation occurs between pictures no. 6 and 7, i. e. between $300 \mu\text{s}$ and $350 \mu\text{s}$ after impact. The bulge is only a few millimeters higher than in Shot No. 10994 at the time of the breakthrough of the projectile. Since no flash X-ray equipment was employed in this, test the residual velocity of the projectile could not be determined. Only an estimate of the expansion velocity of the debris cloud could be derived from the distance-time plots which are displayed in Figure 2.18. Photographs of the target are shown in Figure 2.19. The steel frame at the rear side of the GRP was also strongly deformed. The edges of the frame which were in contact with the GRP were rounded to prevent shear failure. The GRP did not fail at these sites. It is assumed that the possibility to absorb energy by elastic and plastic deformation of the GRP panel was reduced too much by the steel frame, which led to the perforation.

Shot No. 10999

In order to allow sufficient bending of the panel and to prevent GRP layers from being pulled over the nuts triangular shaped steel plate of 10 mm thickness were used instead of washers in the corners of the panel. Bigger washers were used at the central bolts. These modifications can be seen from the photographs of the target which are presented in Figure 2.22. The test was conducted at $v_p = 997$ m/s. The shadowgraphs in Figure 2.20 show that the maximum bulge height was reached during the time interval of observation. This can be seen more clearly from the distance-time plots shown in Figure 2.21. The maximum displacement of the panel was 102 mm and was reached at about $1350 \mu\text{s}$ after impact. The height of the residual static bulge is 54 mm. The photographs of Figure 2.22 show delamination and that GRP layers were also torn around three of the central screws in this test.

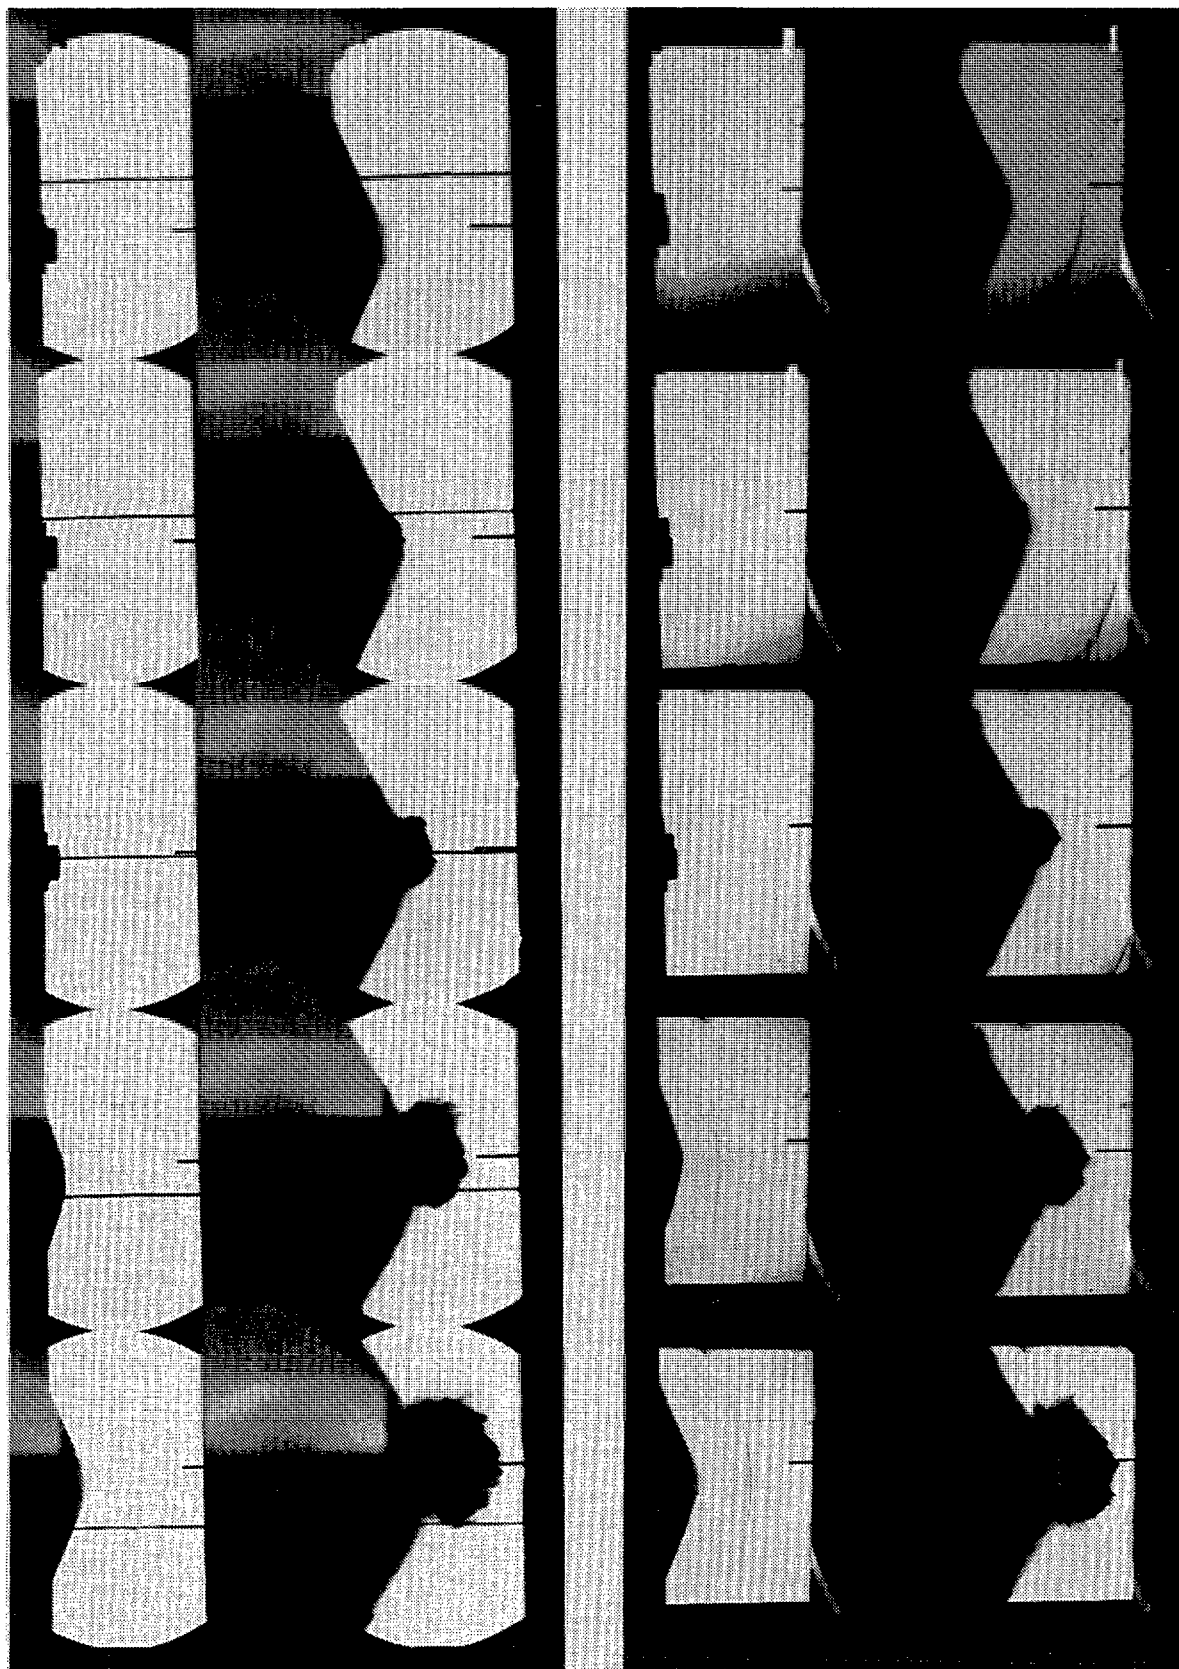

Side view

Top view

Figure 2.17 Shadowgraphs of Shot No. 10998, $v_p = 1001$ m/s,
Cer/GRP 12" x 12"

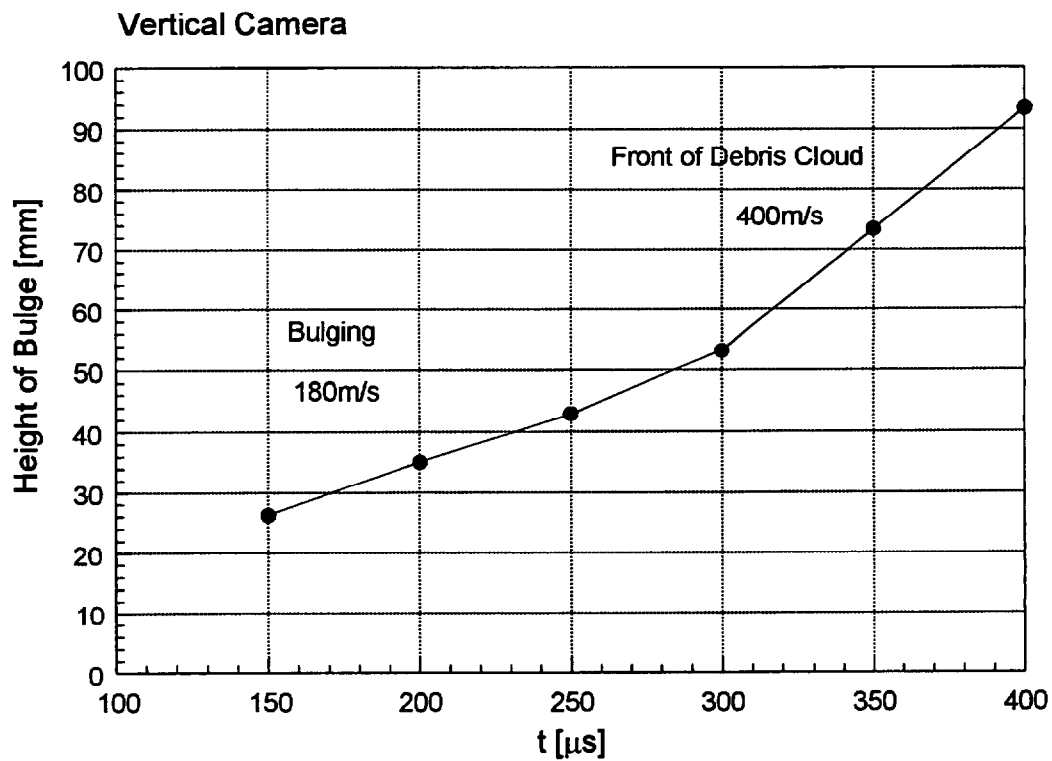
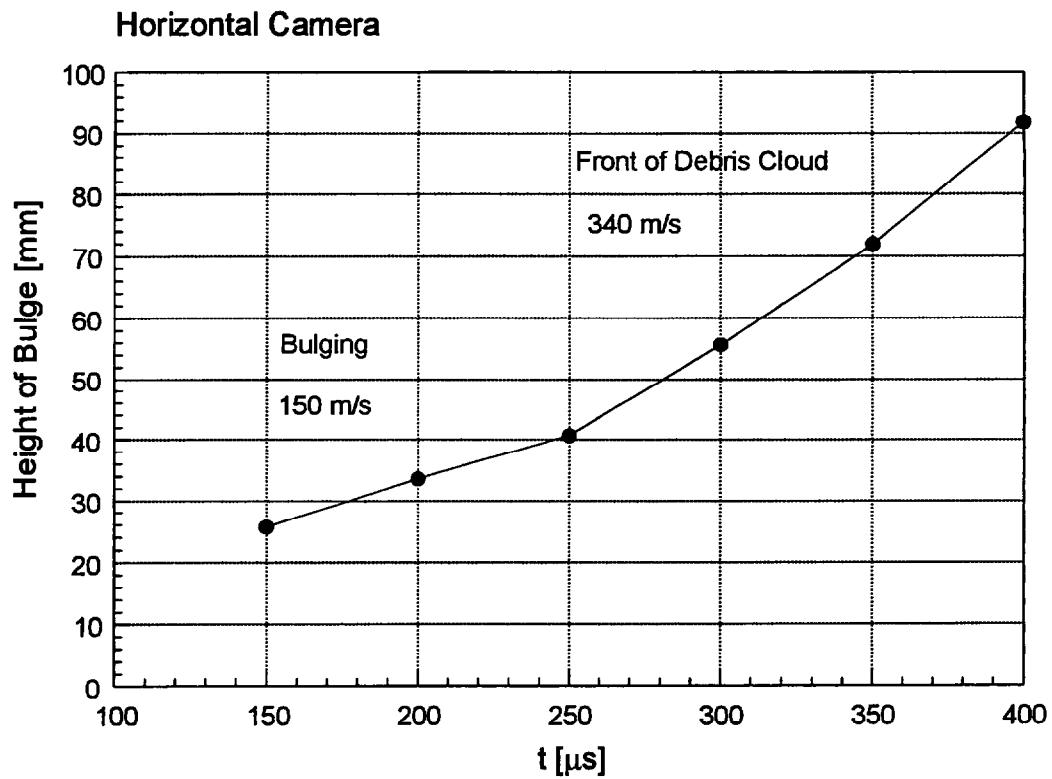


Figure 2.18 Distance-time curves of Shot No. 10998

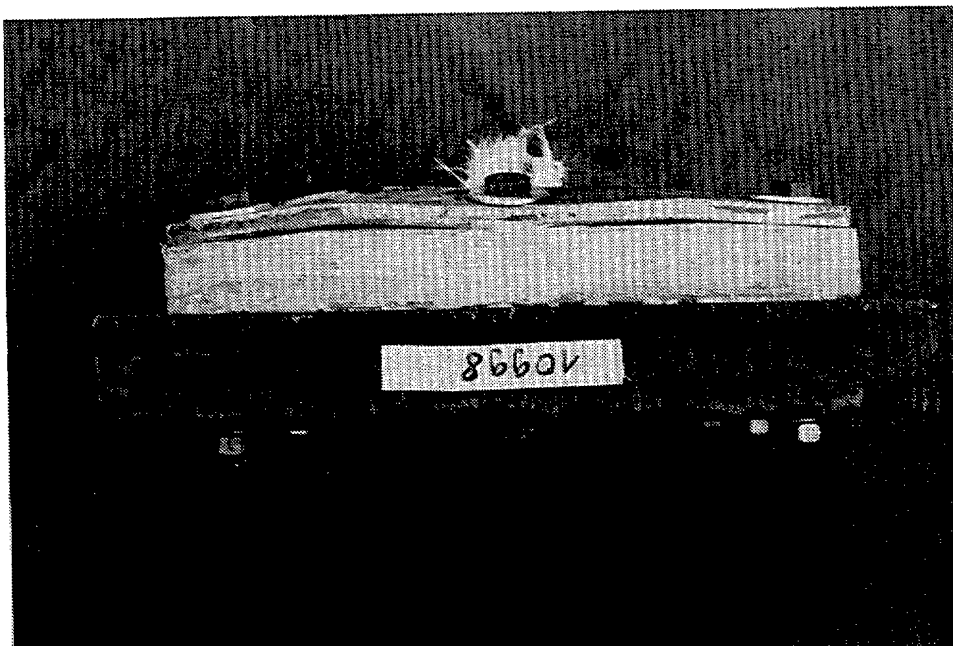
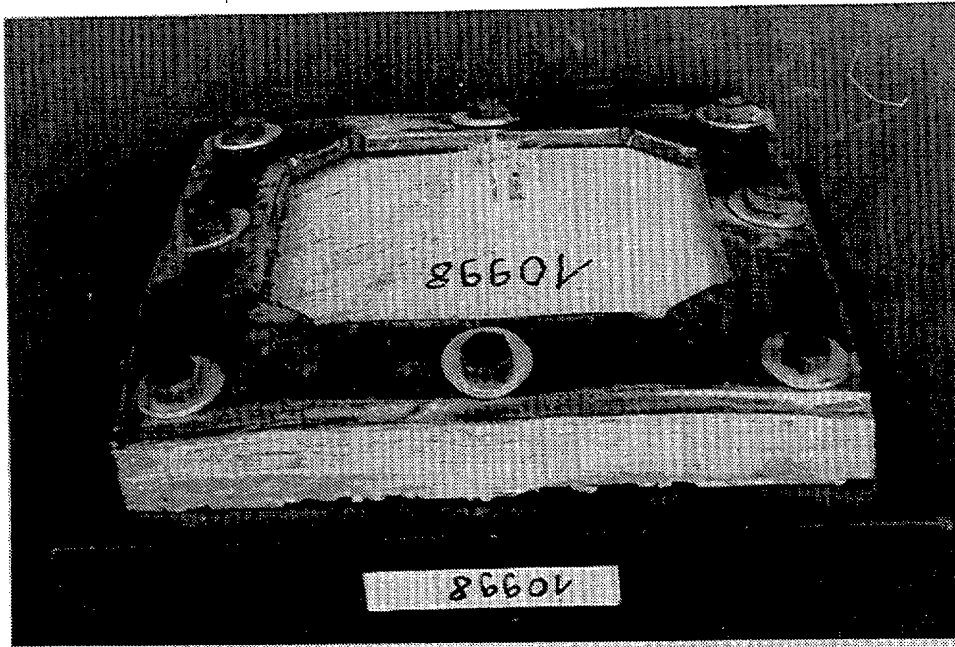


Figure 2.19 Photographs of the impacted target, Shot No. 10998

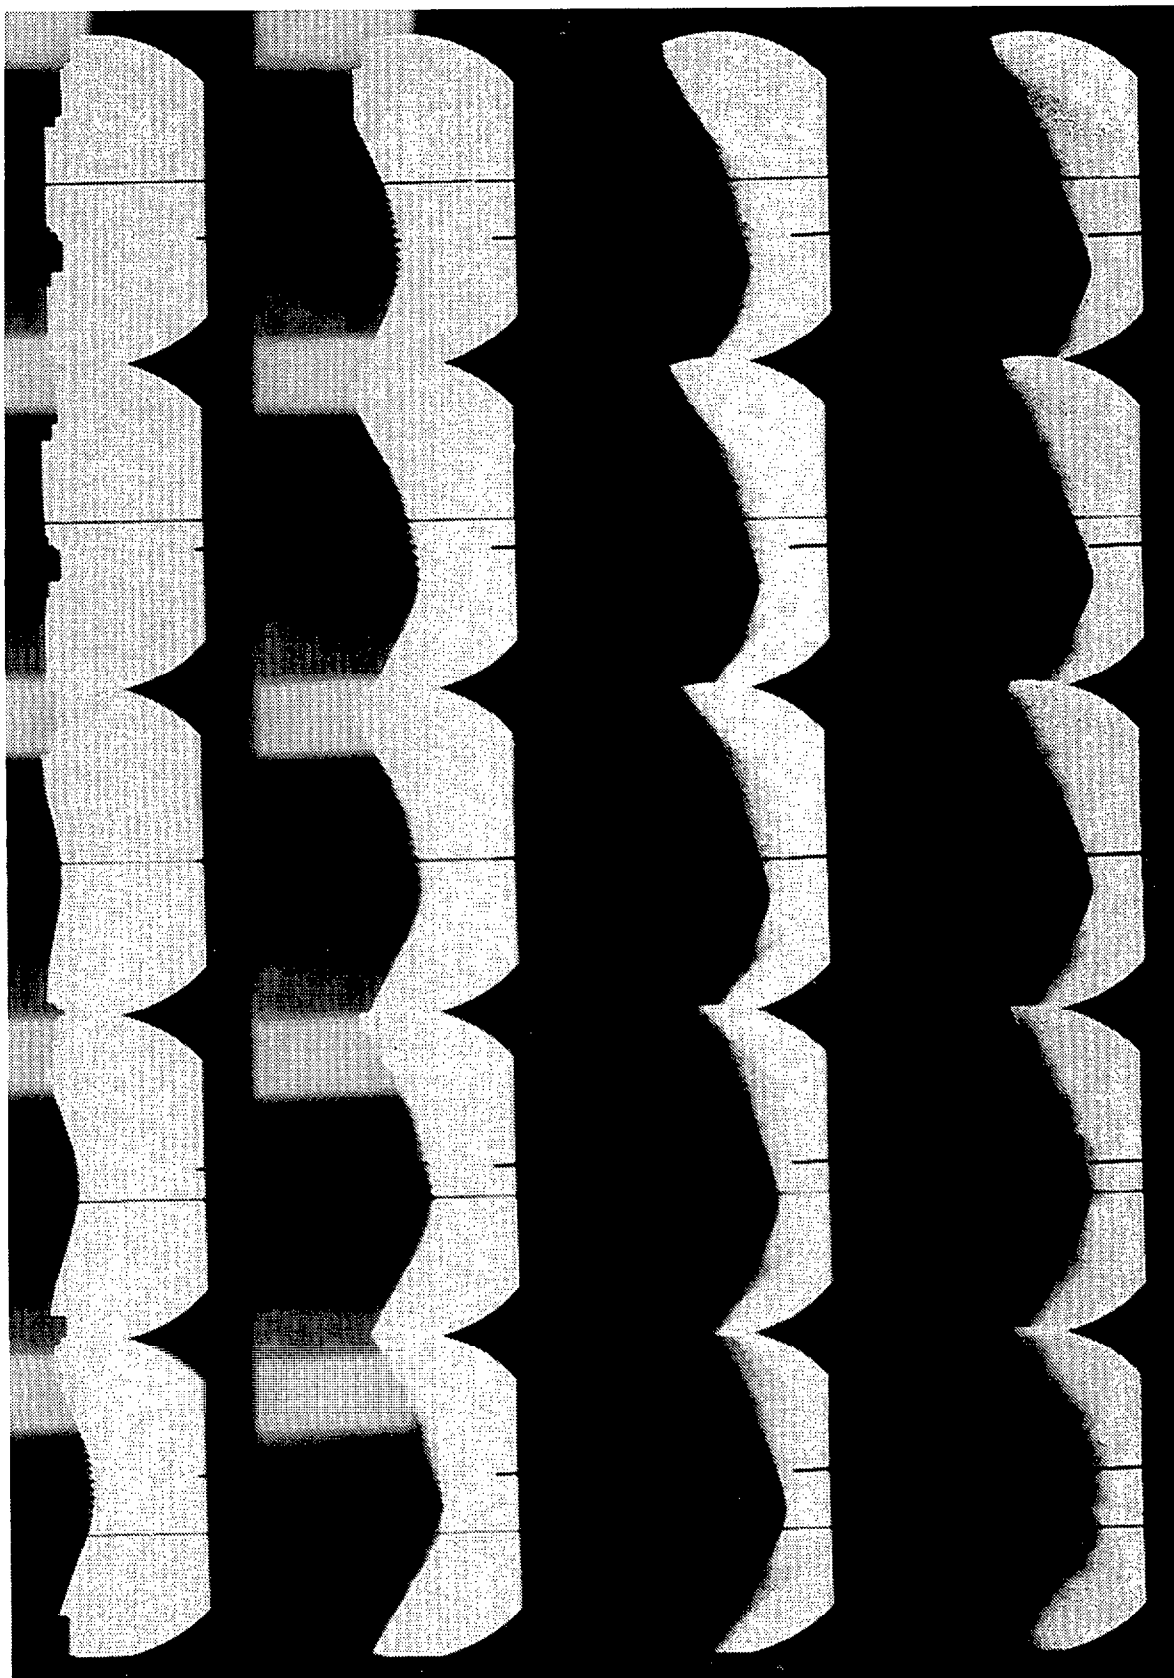


Figure 2.20 Shadowgraphs of Shot No. 10999, side view, $v_p = 997$ m/s, Cer/GRP 12" x 12", total time 1950 μ s

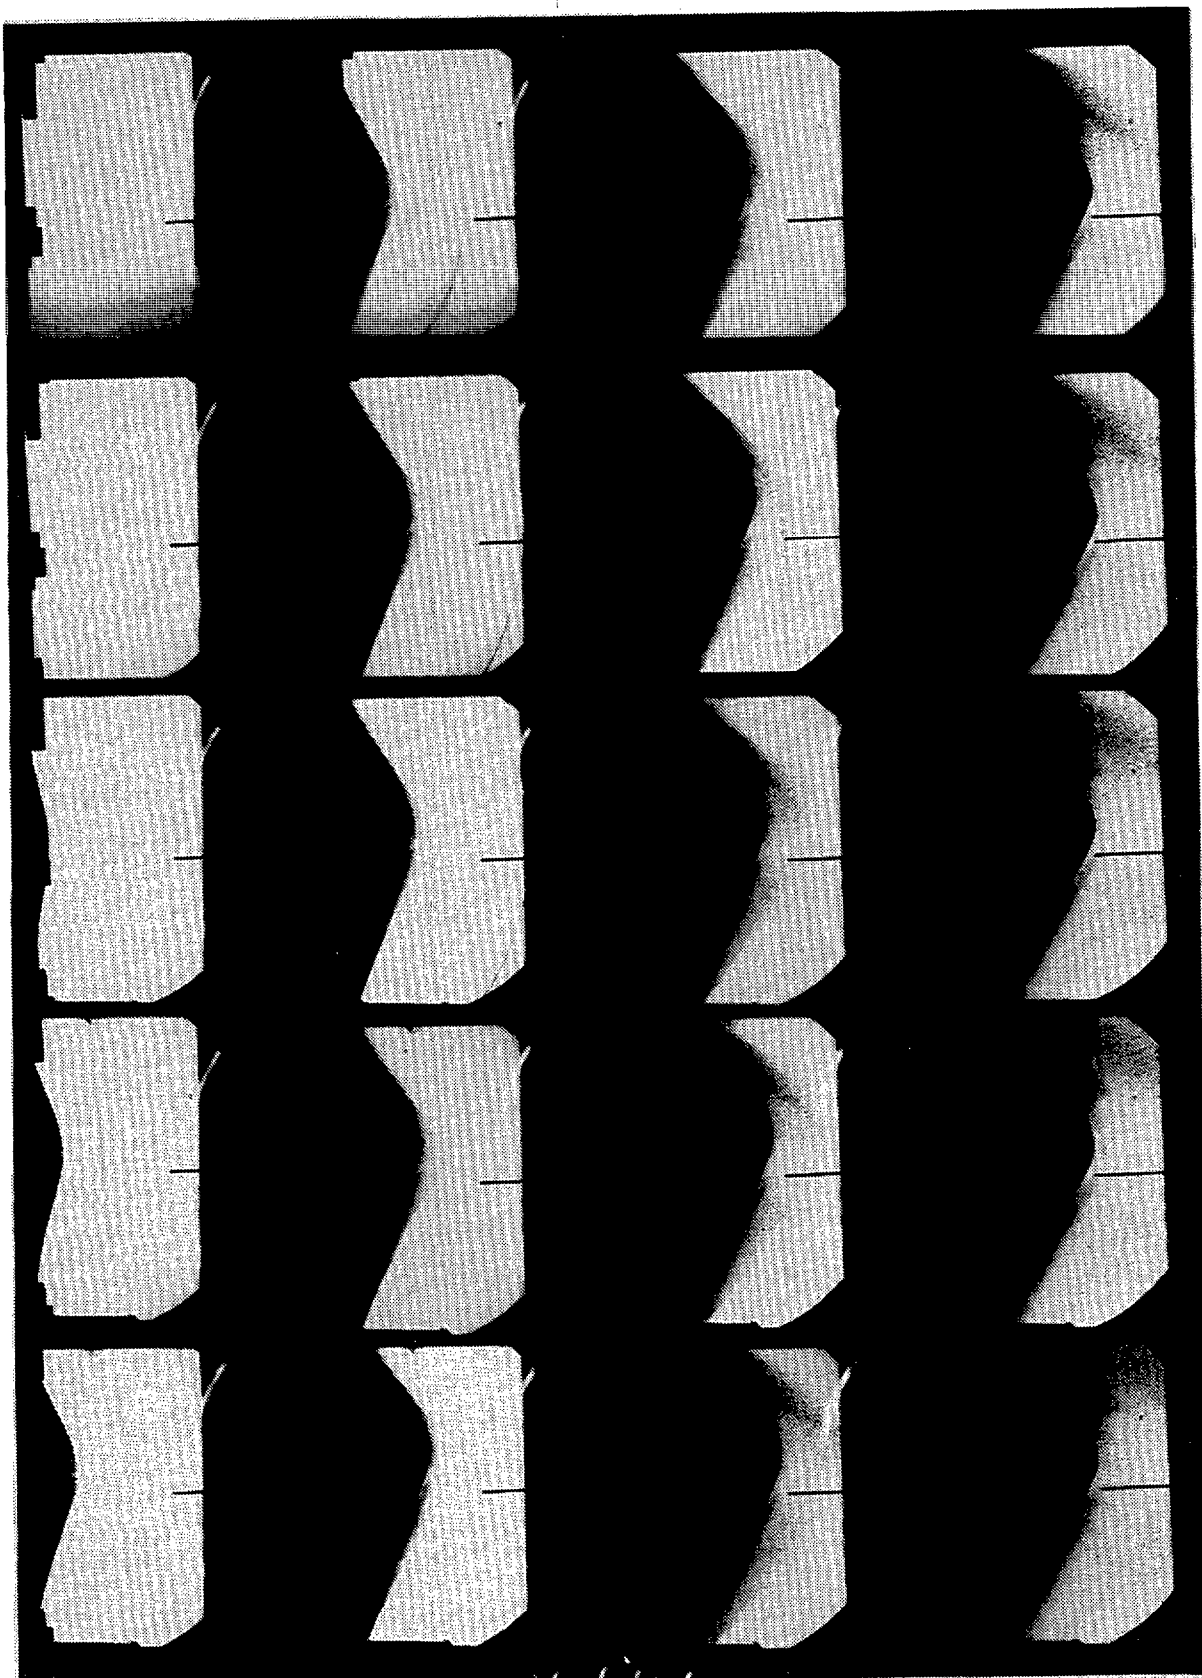


Figure 2.20 Shadowgraphs of Shot No. 10999, top view




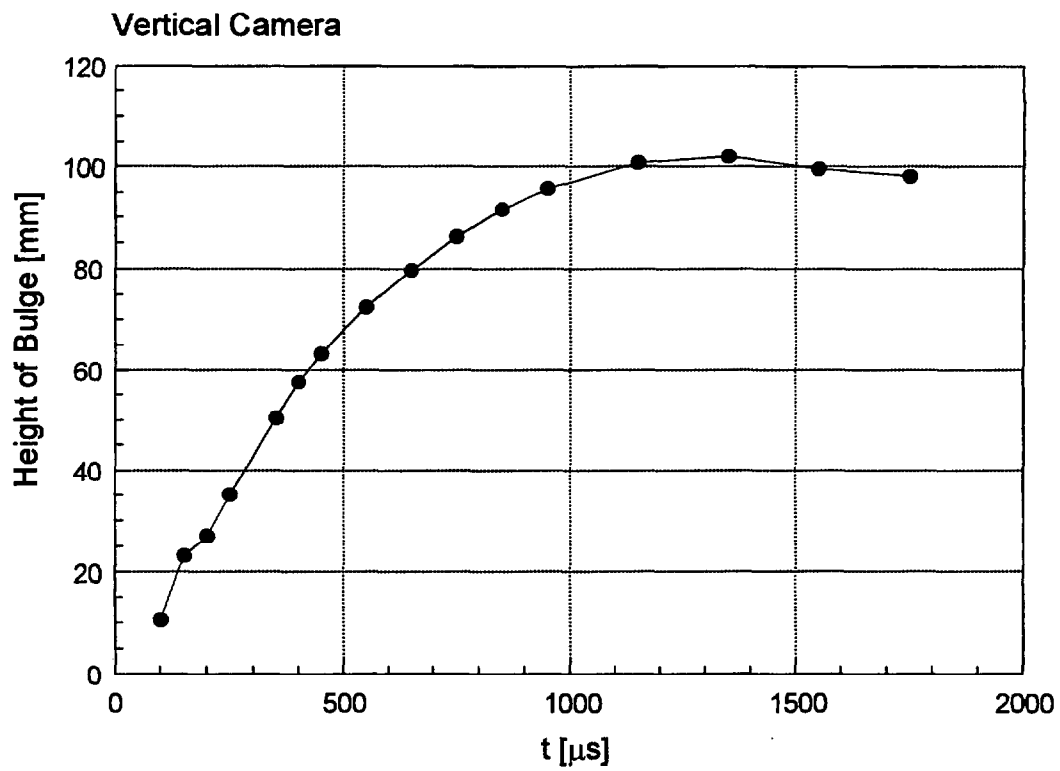


Figure 2.21 Distance-time curves of Shot No. 10999

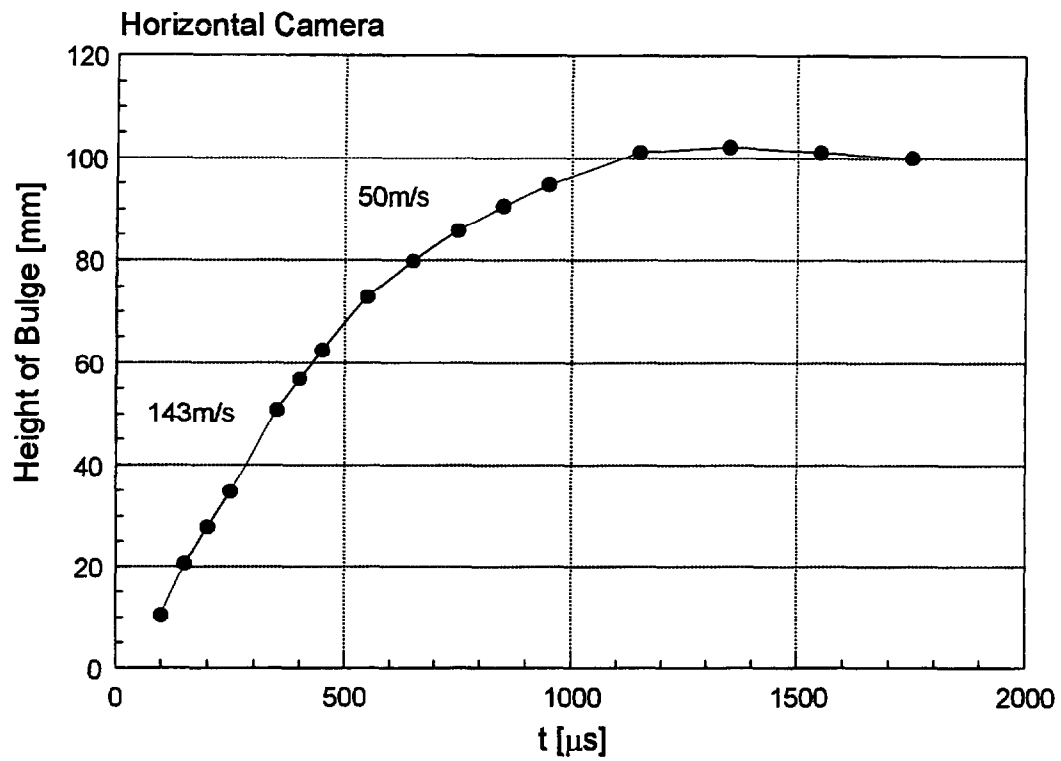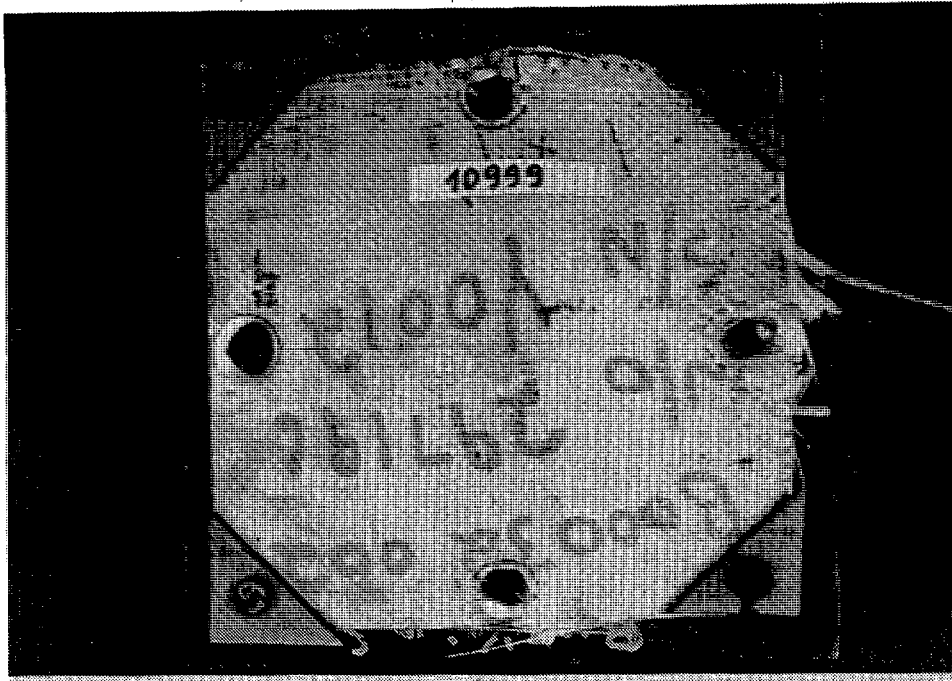

a) Back side

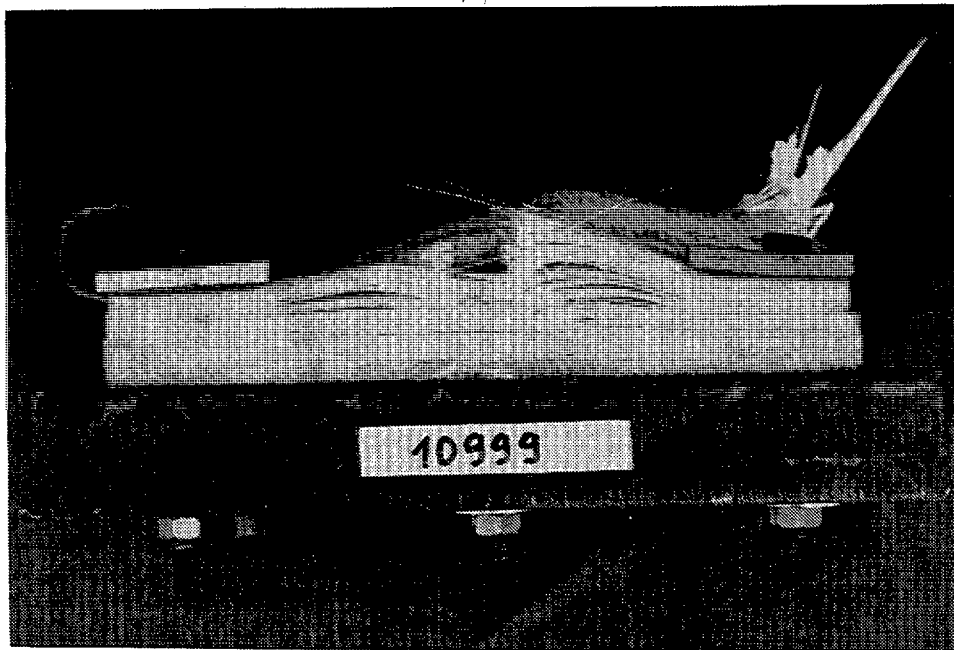

b) Side view

Figure 2.22 Photographs of the impacted target, Shot No. 10999

3 Summary

Ceramic/GRP composites were impacted near their ballistic limit velocity with tungsten alloy projectiles. The bulging of the GRP panels was observed by means of two Craz-Schardin cameras and the distance-time histories of the bulges were derived from the high-speed recordings.

In the case of targets with a GRP backing of the size 24" x 24" the projectile ($v_p = 994$ m/s) could be stopped without visible delamination of the GRP panel. The maximum height of the bulge was 35 mm and was observed between 300 μ s and 400 μ s after impact. The remaining static bulge had a height of 15 mm.

The 12" x 12" GRP panels exhibited a much stronger deformation. The bulge reached a height of about 100 mm after 1.35 ms and a static bulge of 54 mm height remained. Delamination of the GRP panel could not be prevented and part of the layers were torn around the bolts that fixed the target.

In Shot No. 11000, where the projectile perforated the target, a residual velocity of ≈ 640 m/s was measured. If this velocity were taken as an estimate of the penetration velocity the time to penetrate the ceramics would be 62 μ s at most. A bulging of the GRP panels could be recognized for both the 12" panels and the 24" panels not before ≈ 50 μ s after impact. That means that at the time when the bulge begins to form the projectile has already penetrated most part of the ceramics and is strongly eroded. The bulging appears therefore to be primarily caused by the residual projectile. This means that the ceramic tiles are supported by the GRP during penetration for both sizes of the panels. However, the 24" panels can absorb more energy by elastic and plastic deformation and exhibit therefore much less damage after impact.

Acknowledgement

The authors gratefully acknowledge the funding of this work by the U. S. Army Research Laboratory, Aberdeen Proving Ground, MD, USA.

The U. S. Army Research Laboratory would like to acknowledge the assistance of Mr. W. J. Perciballi of Simula Incorporated who assembled the S-2 glass/ceramic laminates for these tests.

INTENTIONALLY LEFT BLANK.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFO CTR ATTN DTIC DDA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218

1	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL OP SD TA 2800 POWDER MILL RD ADELPHI MD 20783-1145
---	---

3	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL OP SD TL 2800 POWDER MILL RD ADELPHI MD 20783-1145
---	---

1	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL OP SD TP 2800 POWDER MILL RD ADELPHI MD 20783-1145
---	---

ABERDEEN PROVING GROUND

5	DIR USARL ATTN AMSRL OP AP L (305)
---	---------------------------------------

NO. OF
COPIES ORGANIZATION

1 HQDA
ATTN SARD TR R CHAIT
PENTAGON
WASHINGTON DC 20310-0103

6 CDR
US ARMY TACOM
ATTN AMSTA TR
J THOMPSON
S GOODMAN
D THOMAS
D HANSEN
M MINNICK
T FURMANIAK
WARREN MI 48397-5000

2 DIR US ARMY RSRCH OFC
ATTN K IYER
J BAILEY
PO BOX 12211
RSRCH TRIANGLE PARK NC
27709-2211

1 CDR NGIC
ATTN W MARLEY
220 SEVENTH AVE
CHARLOTTESVILLE VA
22901-5391

1 CENTRAL INTELLIGENCE AGENCY
ATTN OSWR DSD
W WALTMAN
ROOM 5P0110 NHB
WASHINGTON DC 20505

1 DIR ARPA
ATTN LTC R KOCHER
3701 NORTH FAIRFAX DR
ARLINGTON VA 22203-1714

1 CDR EUROPEAN RSRCH OFC
USARDSG (UK)
ATTN R REICHENBACH
PSC 802 BOX 15
FPO AE 09499-1500

2 DIR LLNL
ATTN R GOGOLEWSKI MS L290
R LANDINGHAM L369
PO BOX 808
LIVERMORE CA 94550

NO. OF
COPIES ORGANIZATION

2 DIR LLNL
ATTN D STEINBERG
J REAUGH L32
PO BOX 808
LIVERMORE CA 94550

2 DIR LANL
ATTN F ADDESSIO
M BURKETT
LOS ALAMOS NM 87545

1 DIR LANL
ATTN
LOS ALAMOS NM 87545

1 JET PROPULSION LABORATORY
ATTN M ADAMS
IMPACT PHYSICS GROUP
4800 OAK GROVE DRIVE
PASADENA CA 91109-8099

2 DIR SNL
ATTN D GRADY MS 0821
D CRAWFORD ORG 1533
PO BOX 5800
ALBUQUERQUE NM 87185

2 DIR SNL
ATTN M FORRESTAL
LUK
PO BOX 5800
ALBUQUERQUE NM 87185

1 DIR SNL
ATTN J ASAY
MS 0548
PO BOX 5800
ALBUQUERQUE NM 87185

2 DIR SNL
ATTN R BRANNON MS 0820
M KIPP MS 0820
PO BOX 5800
ALBUQUERQUE NM 87185

2 UNITED DEFENSE LP
ATTN V HORVATICH
R RAJAGOPAL
PO BOX 359
SANTA CLARA CA 95052-0359

NO. OF
COPIES ORGANIZATION

2 UNITED DEFENSE LP
ATTN M MIDDIONE
J MORROW
PO BOX 359
SANTA CLARA CA 95052-0359

1 UNITED DEFENSE LP
ATTN J JOHNSON
PO BOX 15512
YORK PA 17405-1512

5 IAT
ATTN S BLESS
R SUBRAMANIAN
M NORMANDIA
T KIEHNE
H FAIR
PO BOX 202797
AUSTIN TX 78720-2797

1 ALME AND ASSOCIATES
ATTN M ALME
9650 SANTIAGE ROAD STE 102
COLUMBIA MD 21045

1 NAVAL POST GRADUATE SCHOOL
ATTN J STERNBERG CODE EW
MONTEREY CA 93943

3 UNIV OF DAYTON RSRCH INST
KLA14
ATTN N BRAR
A PIEKUTOWSKI
D GROVE
300 COLLEGE PARK
DAYTON OH 45469-0182

3 LANXIDE ARMOR PRODUCTS
ATTN K LEIGHTON
V KELSEY
R WOLFFE
1300 MARROWS RD
NEWARK DE 19714-6077

1 GENERAL RESEARCH CORP
ATTN A CHARTERS
5383 HOLLISTER AVE
SANTA BARBARA CA 93160-6770

NO. OF
COPIES ORGANIZATION

2 UNIV OF CA SAN DIEGO
DEPT OF APPLIED MECHANICS &
ENGINEERING SERVICES R011
ATTN S NEMAT NASSER
M MEYERS
LA JOLLA CA 92093-0411

4 POULTER LABORATORY
SRI INTERNATIONAL
ATTN D CURRAN
R KLOOP
L SEAMAN
D SHOCKEY
333 RAVENSWOOD AVE
MENLO PARK CA 94025

3 SOUTHWEST RSRCH INST
ATTN C ANDERSON
J RIEGEL
D LITTLEFIELD
6220 CULEBRA RD
SAN ANTONIO TX 78238

1 GEORGIA INST OF TCHNLGY
ATTN K LOGAN
ATLANTA GA 30332-0245

2 AERONAUTICAL RSRCH ASSOC
ATTN R CONTILIANO
J WALKER
50 WASHINGTON RD
PRINCETON NJ 08540

1 CALIFORNIA RSRCH & TECH INC
ATTN D ORPHAL
5117 JOHNSON DR
PLEASANTON CA 94566

1 THE CARBORUNDUM COMPANY
ATTN R PALIA
PO BOX 1054
NIAGARA FALLS NY 19302

3 CERCOM INC
ATTN R PALICKA
A EZIS
G NELSON
1960 WATSON WAY
VISTA CA 92083

NO. OF
COPIES ORGANIZATION

1 BRIGGS COMPANY
ATTN J BACKOFFEN
2668 PETERSBOROUGH ST
HERNDON VA 22071-2443

1 CENTURY DYNAMICS INC
ATTN N BIRNBAUM
7700 EDGEWATER DR
SUITE 626
OAKLAND CA 94621

1 APPLIED RESEARCH ASSOC INC
ATTN J YATTEAU
5941 SO MIDDLEFIELD RD
SUITE 100
LITTLETON CO 801123

1 ZERNOW TECHNICAL SERVICES
ATTN L ZERNOW
425 W BONITA AVE
SUITE 208
SAN DIMAS CA 91773

2 ADELMAN ASSOCIATES
ATTN C CLINE
M WILKENS
3301 EL AMINO RIAL
SUITE 280
ATHERTA CA 94027

1 CYPRESS INTERNATIONAL
ATTN A CAPONECCHI
1201 E ABINGDON DR
ALEXANDRIA VA 22314

3 DOW CHEMICAL INC
ORDNANCE SYSTEMS
ATTN A HART
C HANEY
B RAFANIELLO
800 BUILDING
MIDLAND MI 48667

1 CALKINS R&D INC
ATTN N CALKINS
515 SEWARD PK AVE
ALBUQUERQUE NM 87123

NO. OF
COPIES ORGANIZATION

1 KERAMONT CORPORATION
ATTN E SAVRUN
4231 S FREEMONT AVE
TUSCON AZ 85714

1 KAMAN SCIENCES CORP
1500 GARDEN OF
THE GODS RD
COLORADO SPRINGS CO 80933

1 SAIC
ATTN J FURLONG
MS 264
1710 GOODRIDGE DR
MCLEAN VA 22102

1 BOMBS & WARHEADS BRNCH
MUNITIONS DIVISION
ATTN W COOK
EGLIN AFB FL 32542

2 ALLIANT TECHSYSTEMS INC
ATTN T HOLMQUIST
G JOHNSON
600 SECOND ST NE
HOPKINS MN 55343

2 GDLS
ATTN W BURKE
J ERIDON
38500 MOUND RD
STERLING HEIGHTS MI
48310-3260

1 BATTELLE EDGEWOOD
ATTN A RICCHIAZZI
2113 EMMERTON PARK RD
EDGEWOOD MD 21040

1 CORNING INC
ATTN S HAGG
SP DV 22
CORNING NY 14831

1 COORS CERAMICS COMPANY
STRUCTURAL DIVISION
ATTN R PARICIO
600 NINTH ST
GOLDEN CO 80401

NO. OF
COPIES ORGANIZATION

1 SIMULA INC
ATTN W PERCIBALLI
10016 SOUTH 51 ST
PHOENIX AZ 85044

1 O'GARA HESS & EISENHARDT
ATTN C WILLIAMS
9113 LE SAINT DR
FAIRFIELD OH 45014

1 BROWN UNIVERSITY
DIVISION OF ENGINEERING
ATTN R CLIFTON
PROVIDENCE RI 02912

1 R J EICHELBERGER
409 W CATHERINE ST
BEL AIR MD 21014-3613

1 BOB SKAGGS
RT 11 BOX 81E
SANTA FE NM 87501

1 B EINSTEN
1212 MORNINGSIDE WAY
VENICE CA 90297

NO. OF
COPIES ORGANIZATION

ABERDEEN PROVING GROUND

51 DIR, USARL
ATTN: AMSRL-WT, D ECCLESHALL
AMSRL-WT-T, W MORRISON
AMSRL-WT-TD,
A GUPTA
A DIETRICH JR
T FARRAND
G RANDERS PEHRSON
J WALTER JR
M SCHEIDLER
J SANTIAGO JR
K FRANK
S SEGLETES
M RAFTENBERG
AMSRL-WT-TC,
F GRACE
W WALTERS
R SUMMERS
L MAGNESS
M LAMPSON
K KIMSEY
D SCHEFFLER
G SILSBY
W DE ROSSET
AMSRL WT TA
E HORWATH
E RAPACKI JR
W GILLICH
G FILBEY JR
W BRUCHEY JR
Y HUANG
W GOOCH JR (10 CP)
H MEYER JR
M BURKINS
N RUPERT
T HAVEL
J RUNYEON
M ZOLTOSKI
G BULMASH
AMSRL-WT-WD, A NIILER
AMSRL-WT-T, T WRIGHT
AMSRL-MD-PD,
S CHOU
D DANDEKAR
J MACKIEWICZ
R RAJENDRAN
AMSRL-MD-P, D VIECHNICKI

NO. OF
COPIES ORGANIZATION

- 3 FRANHOFER INSTITUT FÜR
KURZZEITDYNAMIK
ERNST MACH INSTITUT
ATTN H SENF
E STRAßBURGER
H ROTHENHÄUSLER
HAUPTSTRASSE 18
D 79 576 WEIL AM RHEIN
GERMANY
- 3 FRANHOFER INSTITUT FÜR
KURZZEITDYNAMIK
ERNST MACH INSTITUT
ATTN G SCHRÖDER
A STILP
V HOHLER
ECKERSTRASSE 4
D 79 104 FREIBURG
GERMANY
- 3 DEUTSCH FRANZÖSISCHES
FORSCHUNGSINSTITUT SAINT LOUIS
ATTN H ERNST
H LERR
K HOOG
CÉDEX 5 RUE DU GÉNÉRAL
CASSAGNOU
F 68301 SAINT LOUIS
FRANCE
- 6 DEFENCE RESEARCH AGENCY
ATTN W CARSON
T HAWKINS
B SHRUBSALL
C FREW
I CROUCH
B JAMES
CHOBHAM LANE
CHERTEY SURREY KT16 OEE
UNITED KINGDOM
- 1 DEFENCE RESEARCH AGENCY
ATTN T BARTON
FT HALSTEAD SEVEN OAKS
KENT TN14 7BP
UNITED KINGDOM
- 1 BATTELLE INGENIEURTECHNIK GMBH
ATTN W FUCKE
DUESSELDORFLER STR 9
D 65760 ESCHBORN
GERMANY

NO. OF
COPIES ORGANIZATION

- 1 DEUTSCHE AEROSPACE AG
ATTN M HELD
POSTFACH 13 40
D 86 523 SCHROBENHAUSEN
GERMANY
- 5 RAPHAEL BALLISTICS CENTER
ATTN Y PARTOM
G ROSENBERG
M MAYSELESS
Z ROSENBERG
Y YESHURUN
BOX 2250
HAIFA 31021
ISRAEL
- 1 DYNAMEC RESEARCH AB
ATTN Å PERSSON
PARADISGRÄND 7
S 151 36 SÖDERTÄLJE
SWEDEN
- 1 DEFENCE RESEARCH ESTABLISHMENT
SUFFIELD
ATTN C WEICKERT
BOX 4000
MEDICINE HAT ALBERTA T1A 8K6
CANADA
- 6 CENTRE DE RECHERCHES ET D'ETUDES
D'ARCUEIL
ATTN F TARDIVAL
C COTTENNOT
S JONNEAUX
H ORSINI
D BOUVART
S SERROR
16 BIS AVENUE PRIEUR DE LA CÔTE D'OR
F 94114 ARCUEIL CÉDEX
FRANCE
- 1 INGENIEURBÜRO DEISENROTH
ATTN F DEISENROTH
AUF DE HARDT 33 35
D 5204 LOHMAR 1
GERMANY
- 1 CONDAT
ATTN J KIERMEIR
MAXILLANSTR 28
8069 SCHEYERN FERNHAG
GERMANY

NO. OF
COPIES ORGANIZATION

- 1 UNIVERSITÄT DER
BUNDESWHER MÜNCHEN
ATTN K THOMA
D-85577 NEUBIBERG
GERMANY
- 1 R OGORKIEWICZ
18 TEMPLE SHEEN
LONDON SW 14 7RP
UNITED KINGDOM
- 3 SWEDISH DEFENCE RESEARCH
ESTABLISHMENT
ATTN B JANZON
I MELLGARD
L HOLMBERG
BOX 551
S 147 25 TUMBA
SWEDEN
- 2 TNO PRINS MAURITS LABORATORY
ATTN H PASMAN
R YSSELSTEIN
PO BOX 45
2280 AA RIJSWIJK
LANGE KLEIWEG 137
RIJSWIJK NETHERLANDS
- 2 DEFENCE TECHNOLOGY AND
PROCUREMENT AGENCY
ATTN G LAUBE
W ODERMATT
BALLISTICS WEAPONS AND COMBAT
VEHICLE TEST CENTER
CH 3602 THUN
SWITZERLAND
- 1 CELSIUS MATERIALTEKNIK
KARLSKOGA AB
ATTN L HELLNER
S 691 80 KARLSKOGA
SWEDEN
- 1 SWISS FEDERAL ARMAMENT WORKS
ATTN W LANZ
ALLMENDSSTRASSE 86
CH 3602 THUN
SWITZERLAND

NO. OF
COPIES ORGANIZATION

- 2 HIGH ENERGY DENSITY RESEARCH
CENTER
ATTN G KANEL
V FORTOV
IZHORSKAYA 13 19
MOSCOW 127412
RUSSIAN REPUBLIC
- 1 EMBASSY OF AUSTRALIA
ATTN R WOODWARD
COUNSELLOR DEFENCE SCIENCE
1601 MASSACHUSSETTS AVE NW
WASHINGTON DC 20036-2273
- 1 IOFFE PHYSICO TECHNICAL INSTITUTE
ATTN A KOZHUSHKO
ST PETERSBURG 194021
RUSSIAN REPUBLIC
- 3 AERONAUTICAL & MARITIME RSRCH LAB
ATTN N BURMAN
S CIMPOERU
D PAUL
PO BOX 4331
MELBOURNE VIC 3001
AUSTRALIA
- 1 TECHNION INSTITUTE OF TECHNOLOGY
FACULTY OF MECHANICAL ENGINEERING
ATTN S BODNER
TECHNION CITY
HAIFA 32000
ISRAEL
- 2 FEDERAL MINISTRY OF DEFENCE
DIRECTORATE OF EQUIPMENT AND
TECH LAND
RÜ V 2
ATTN D HAUG
L REPPER
POSTFACH 1328
53003 BONN
GERMANY
- 3 CENTER D'ÉTUDES GRAMAT
ATTN J CAGNOUX
C GALLIC
J TRANCHET
46500 GRAMAT
FRANCE

NO. OF
COPIES ORGANIZATION

- 1 ROYAL NETHERLANDS ARMY
ATTN J HOENEVELD
V D BURCHLAAN 31
PO BOX 90822
2509 LS THE HAGUE
NETHERLANDS
- 1 ROYAL MILITARY ACADEMY
ATTN E CELENS
RENAISSANCE AVE 30
B-1040 BRUSSEL
BELGIUM
- 1 MORGAN MATROC
ATTN C ROBERSON
ST PETERS RD RUGBY
WARWICKSHIRE CV21 3QR
UNITED KINGDOM
- 1 OTO BRED A
ATTN M GUALCO
VIA VALDIOCCHI, 15
I-19136 LA SPEZIA
ITALY
- 3 SNPE
ATTN P FABRE
C GOUZOU GUEN
C GAUDIN
B.P. NO. 2
91710 VERT-LE-PETIT
REPUBLIC OF FRANCE
- 3 TECHNISCHE UNIVERSITÄT
CHEMNITZ-ZWICKAU
ATTN L MEYER
I FABER
L KRUEGER
SCHEFFEL STR 110
09120 CHEMNITZ
GERMANY
- 1 ETBS/DSTI
ATTN P BARNIER
ROUTE DE GUERAY
BOITE POSTALE 712
18015 BOURGES CEDEX
REPUBLIC OF FRANCE

NO. OF
COPIES ORGANIZATION

- 2 NATIONAL DEFENCE RESEARCH
ESTABLISHMENT
ATTN S SAVAGE
J ERIKSON
FOA 630
S-172 90 STOCKHOLM
SWEDEN